

ARMY RESEARCH LABORATORY



An Equation of State for Metals

by Steven B. Segletes

ARL-TR-1270

November 1996

DTIC QUALITY INSPECTED 2

19970131 030

Approved for public release; distribution is unlimited.

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer need. Do not return it to the originator.

Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5066

ARL-TR-1270

November 1996

An Equation of State for Metals

Steven B. Segletes

Weapons and Materials Research Directorate, ARL

Abstract

A new analytical equation of state is offered for metals. The form is expressible completely in terms of the maximum lattice vibration frequency, macroscopically expressible as the characteristic temperature, Θ , and its derivatives. For one particularly useful special case, the results have been found to match both cold-curve and shock-Hugoniot data for a variety of metals. The equation is of the Grüneisen variety, in which the Grüneisen parameter is specified as a function of volume only. The equation begins to lose accuracy in the pressure range of one to several megabars, perhaps because of the breakdown of the Grüneisen assumption, whereupon the Grüneisen parameter becomes energy dependent.

ACKNOWLEDGMENTS

The author would like to express a great deal of gratitude to Mr. Konrad Frank and Dr. Andrew Dietrich, both of the U.S. Army Research Laboratory, for their moral and intellectual support of this work, which occurred during the inspirational 2 1/2 week period between 18 July 1996 and 5 August 1996. In addition, the author would like to thank Dr. William P. Walters, also of ARL, for his thoughtful review of the work and Dr. Gerald I. Kerley of Albuquerque, NM, for his helpfulness in supplying several material parameters at the onset of this work.

INTENTIONALLY LEFT BLANK

TABLE OF CONTENTS

	<u>Page</u>
ACKNOWLEDGMENTS	iii
LIST OF FIGURES	vii
1. INTRODUCTION	1
2. BACKGROUND	1
3. THE GRÜNEISEN ASSUMPTION	4
4. THE MODEL	8
5. A USEFUL SIMPLIFICATION	11
6. COMPARISON TO THE UCC MODEL	13
7. COMPARISON TO DATA	16
8. CONSTRAINTS ON THE FREE PARAMETER $\Gamma_0 \psi'$	21
9. CONCLUSIONS	22
10. REFERENCES	35
DISTRIBUTION LIST	39
REPORT DOCUMENTATION PAGE	55

INTENTIONALLY LEFT BLANK

LIST OF FIGURES

<u>Figure</u>	<u>Page(s)</u>
1. Relative Grüneisen parameter versus relative volume as a function of parameter $\Gamma_0 \psi'$, taken in increments of 0.2, for the assumed form $\psi'' = 0$	24
2. Comparison of binding energy of current model to that of Rose <i>et al.</i> [1], for given anharmonicities. Rose curve depicted with dark line. Current model shown in dashed lines for incremental values of $\Gamma_0 \psi'$, ranging from 0 to 1 in increments of 0.2. (a) $\eta = 3$. (b) $\eta = 4$. (c) $\eta = 5$. (d) $\eta = 6$. (e) $\eta = 7$. (f) $\eta = 8$. (g) $\eta = 9$	24-27
3. Comparison of binding energy of the current model to that of Rose <i>et al.</i> [1], for given values of $\Gamma_0 \psi'$ parameter. Rose curve depicted with dark line. Current model shown in dashed lines for integral values of η , ranging from 3 to 9. (a) $\Gamma_0 \psi' = 0.6$. (b) $\Gamma_0 \psi' = 0.7$. (c) $\Gamma_0 \psi' = 0.8$. (d) $\Gamma_0 \psi' = 0.9$. (e) $\Gamma_0 \psi' = 1.0$	28-30
4. Cold-curve fit with Hugoniot prediction for silver, to 2 Mbar. Cold data [22] (filled symbols) and Hugoniot data [18, 19] (unfilled symbols) included.	30
5. Cold-curve fit with Hugoniot prediction for aluminum, to 9 Mbar. Cold data [23] (filled symbols) and Hugoniot data [19, 24] (unfilled symbols) included. Dashed curve is Hugoniot prediction, assuming $\Gamma_0 = 1.2$	31
6. Cold-curve fit with Hugoniot prediction for copper, to 5 Mbar. Cold data [22] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.	31
7. Cold-curve fit for lithium, to 0.8 Mbar. Cold data [1] (filled symbols) and Hugoniot data [18] (unfilled symbols) included.	32
8. Cold-curve fit with Hugoniot prediction for molybdenum, to 2 Mbar. Cold data [22] (filled symbols) and Hugoniot data [19] (unfilled symbols) included. . . .	32
9. Cold-curve fit with Hugoniot prediction for palladium, to 2.5 Mbar. Cold data [22] (filled symbols) and Hugoniot data [18] (unfilled symbols) included. . . .	33
10. Cold-curve fit with Hugoniot prediction for platinum, to 8 Mbar. Cold data [1] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.	33

LIST OF FIGURES (CONTINUED)

<u>Figure</u>	<u>Page</u>
11. Cold-curve fit for rubidium, to 0.4 Mbar. Cold data [1] (filled symbols) and Hugoniot data [18] (unfilled symbols) included.	35
12. Cold-curve fit with Hugoniot prediction for 304 stainless steel (70% Fe, 19% Cr, 11% Ni), to 5 Mbar. Cold data [1] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.	35

1. INTRODUCTION

An analytical equation of state, satisfying the Grüneisen assumption, was developed for metals, which matches available cold-curve and Hugoniot data for a variety of metals out to pressures in the megabar regime. The model uses the Universal Cold Curve (UCC) model of Rose *et al.* [1] as its inspiration, rather than being derived from first principles. The UCC model matches cold-compression data for a variety of metallic elements, over wide ranges of pressure into the megabar range. However, unlike the UCC model, which only gives pressure along the zero-degree isotherm (*i.e.*, the cold curve) in terms of a density variable, the currently offered model is expressible in terms of higher-level thermodynamic functions (namely, the maximum lattice vibrational frequency, ω_{max} , macroscopically expressible as the characteristic temperature, $\Theta(V)$, and its derivatives). The current model therefore allows the calculation of state changes along any thermodynamic path, not only that of isothermal, cold compression. Unlike other follow-on models to Rose *et al.*, such as Vinet *et al.* [2, 3] and Baonza *et al.* [4, 5], the current model's thermal component is coupled to the lattice compression component in a unified way, precisely because the lattice compression component is expressed in terms of frequency, not compression. The general form of the current model requires the specification of the characteristic temperature (*i.e.*, lattice frequency) with volume; however, one particular form for $\Theta(V)$ has been employed, with very good resulting agreement to both cold-curve and shock-Hugoniot data for metals. As a note of warning though, the use of the model for materials undergoing phase change has not been validated, and is not therefore encouraged.

2. BACKGROUND

The UCC model [1] does a truly remarkable job of matching cold-compression data for a variety of solid elements, over wide ranges of pressure into the megabar range. The

UCC model also predicts the tensile pressure in materials under cold expansion out to rather large distentions. The UCC model expresses the cold energy as

$$E_c = E_b [1 - (1 + a + 0.05 a^3) \exp(-a)] , \quad (1)$$

where E_b is the specific lattice binding energy, and a is a dimensionless parameter defining the relative spacing of the lattice atoms, given by

$$a = \eta \left((V/V_0)^{1/3} - 1 \right) . \quad (2)$$

In eqn. (2), the parameter η is called the anharmonicity factor and V and V_0 are the current and ambient specific volumes of the material, respectively. The anharmonicity factor represents a ratio of lengths on the atomic scale, but may be expressed in terms of macroscopic parameters as

$$\eta = 3 \frac{C_0}{\sqrt{E_b}} , \quad (3)$$

where C_0 is the bulk sound speed in the material at zero pressure and absolute temperature. Note that the use of the adiabatic, bulk sound speed is justified, even though Rose *et al.* [1] express their result in terms of the *isothermal* bulk modulus, since the zero-degree isotherm is also an isentrope.

Since the cold curve is not only an isotherm but also an isentrope, the cold pressure, p_c , is obtainable simply as the negative of the derivative of the cold energy ($-dE_c/dV$). The UCC model is essentially a well-reasoned empirical fit to data derived from first-principle models of cohesive energies expressed as a function of lattice spacing. By clever construct, Rose *et al.* [1] developed the nondimensional parameter a , which effectively scales the cold curve for all solids onto the same metric. When applied to available macroscopic cold-compression data for a variety of materials, the model provides an extremely accurate description of available data, encompassing pressures out to one and, in some cases, several megabars.

Since the publication of the the UCC model by Rose *et al.* [1], there have been further advances following the lines of their work. Vinet *et al.* [2, 3] successfully introduced temperature effects into the context of the earlier work. It was shown that the form of Rose was valid, not only for zero temperature, but for any isotherm. The model of Vinet thus became an isothermal equation of state, and temperature effects were accounted for by modeling the variation of bulk modulus with temperature. Though not explicitly casting their work in Grüneisen form, they do so implicitly by citing that "it has been observed experimentally that above the Debye temperature, [thermal pressure] is a linear function of T." By adding to this observation that above the Debye temperature, thermal energy is likewise linear in T, one may conclude that $V(\partial p/\partial E)_V = \Gamma$ (the Grüneisen parameter) is thus constant for fixed V. In both works of Vinet *et al.*, the temperature dependence of the bulk modulus was linearly fit to data for several substances. With this linear fitting form, they showed that their equation of state could reproduce the Murnaghan equation of state.

Very recent works by Baonza *et al.* [4, 5] have been able to advance the field by expressing the compressibility of dense phases using an inverse power law as a function of the divergence pressure along a certain pseudospinodal curve at the considered temperature.

To obtain a general equation of state at points off the pseudospinodal, they too, like their predecessor Vinet, model the thermal pressure deviations from this reference curve using a Grüneisen law, though in their case, it is one in which the Grüneisen law is assumed to follow a commonly used form—namely, $(\Gamma/V) = \text{fitted constant}$.

A key distinction, however, between the work of Vinet *et al.* [2, 3], Baonza *et al.* [4, 5] and what will be proposed in the current work is that, in the works of Vinet and Baonza, the function governing the Grüneisen reference curve behavior (an isotherm in the case of Vinet, the zero pseudospinodal curve in the case of Baonza) and that governing temperature (*i.e.*, thermal pressure) effects are functionally independent. There is no unifying precept tying the two functions together. By contrast, the current work will predict volumetric and thermal effects with a single unified function. Volumetric effects are defined through the characteristic temperature function, Θ , and thermal effects (via internal energy, E) are defined via the ψ function (related to the Grüneisen function by $\psi=V/\Gamma$), and are thus inextricably linked to Θ by definition. In essence, specification of the cold curve in the context of the current model defines the thermal behavior, or alternately, specification of the Grüneisen function for thermal behavior defines the cold curve. The key to this advance over prior work is modeling the cold curve, not in terms of density, as do Vinet and Baonza, but doing so in terms of lattice frequency, as did Debye and Einstein.

3. THE GRÜNEISEN ASSUMPTION

The characteristic temperature, Θ , is an important thermodynamic parameter. The best model existing to date for it is the Debye temperature, Θ_D . The characteristic temperature is central to the question of how the constant-volume specific heat varies with temperature, from the high temperature limit of three times the universal gas constant per mole (known as the law of Dulong and Petit [6]) to a value of zero at absolute zero temperature. The derivation

of specific heat is based on quantum statistical mechanics and depends on the frequency distribution of vibration modes, ω_i , within the crystal lattice. In 1907, Einstein proposed that all permissible vibrational modes are simultaneously excited with temperature, and he derived a specific heat expression that was qualitatively correct, but which approached zero in too rapid of a manner at absolute zero temperature. Debye remedied this deficiency in 1912 by proposing a more realistic frequency distribution of vibrational modes [6]. Common to all of these models is the notion of a characteristic temperature, by which the physical temperature, T , may be scaled in order to achieve the dimensionless temperature parameter, (Θ/T) , through which the specific heat is expressed. In all of these models, including that of Debye, the characteristic temperature is directly proportional to the maximum excited frequency mode, ω_{max} .

As Desloge [7] points out though, the characteristic temperature is itself a function of volume [*i.e.*, $\Theta = \Theta(V)$]. The variation of Θ with V is really a macroscopic manifestation of the variation of vibrational frequencies ω_i with V . But since specific heat theory indicates that "the frequency spectrum is entirely determined by the limiting frequency ω_{max} . . . all other oscillations change their frequencies in the same ratio [as ω_{max}] [8]." Thus, the log-derivative of any arbitrary vibrational mode with volume is the same as the log-derivative of the limiting frequency, ω_{max} , namely

$$-\frac{d \ln \omega_i}{d \ln V} = -\frac{d \ln \omega_{max}}{d \ln V} . \quad (4)$$

This condition quantifies the Grüneisen assumption. Not unexpectedly, its value is known as the Grüneisen parameter, denoted by

$$\Gamma = -\frac{d \ln \omega_{\max}}{d \ln V} . \quad (5)$$

Of course, it is more common to see this parameter expressed in terms of macroscopic thermodynamic state variables as

$$\Gamma = V \left(\partial p / \partial E \right)_V . \quad (6)$$

The notion that all vibrational frequencies change with volume in the same ratio as the limiting frequency is fundamental to Grüneisen theory. The alternative is that each vibrational mode would have its own associated Grüneisen parameter, Γ_i , and the aggregate macroscopic effect would necessarily be an average over all of the individual Γ_i , weighted in some manner by the fractional energy component associated with each mode. Such an aggregate Γ would not only vary with volume, but also with thermal energy, as the fractional energy component associated with each mode was redistributed with increasing temperature. In fact, Grodzka [9] summarizes work that suggests there is a significant decrease in the Grüneisen parameter with thermal energy. Similarly, very high pressure equation-of-state theories, which include electronic effects, are clear departures from Grüneisen theory.

Since, however, non-Grüneisen theory is beyond the scope of the current effort, we limit the discussion to materials obeying the constraint of eqn. (4). Since both the characteristic temperature and the Grüneisen parameter are related to the limiting vibration frequency of the lattice, ω_{\max} (Θ directly proportional to ω_{\max} and Γ related through eqn. [5]), Θ and Γ are, in fact, related to each other as follows:

$$\frac{\Theta'}{\Theta} = -\frac{1}{\psi}, \quad (7)$$

where the prime denotes differentiation with respect to specific volume, and the state variable ψ , defined as V/Γ , has been introduced [10, 11] for convenience in manipulating the thermodynamic equations. The functional form of the Grüneisen parameter will define the quantitative relationship expressed in eqn (7). For example, if Γ is a constant, independent of volume, then

$$\Theta V^{\Gamma_0} = \text{constant} \quad (\text{when } \Gamma \text{ constant}).$$

If, on the other hand, ψ is held constant [i.e., $\Gamma = \Gamma_0/(1+\mu)$, where $\mu = (V_0 - V)/V$], then

$$\Theta e^{\Gamma} = \text{constant} \quad (\text{when } \psi \text{ constant}).$$

Finally, if ψ is linear in V , such that ψ' is held constant [i.e., $\Gamma = \Gamma_0/(1+\beta\mu)$], as

Segletes [12] proposed for reasons of thermodynamic stability, then

$$\Theta \psi^{(1/\psi')} = \text{constant} \quad (\text{when } \psi' \text{ constant}).$$

This last Grüneisen form is equivalent to that known as the Sesame formula [13]. Each unique expression for Γ will produce a unique algebraic relationship between Γ and Θ , though each will satisfy the differential relationship of eqn. (7).

The Grüneisen equation of state, which follows from the Grüneisen assumption, may be expressed in a variety of ways, but amounts to the following:

$$P - P_{ref} = (E - E_{ref})/\psi \quad . \quad (8)$$

In this equation, the reference functions are the pressure and specific internal energy states along a known reference curve, such as an isotherm, isentrope, or Hugoniot. One of the historical problems with estimating the Grüneisen function has been that it was usually inferred by using hard experimental data along one thermodynamic path (*e.g.*, the Hugoniot) and comparing it to *predictions* of thermodynamic states along another path [14–16] (usually the cold curve predicted by models of Slater [8], Dugdale and McDonald [17], or others). In this sense, previous nonambient Grüneisen values were not even obtained by indirect measurement, but rather were back-calculated by assuming the validity of a particular cold-curve model. Grodzka [9] cleverly displayed the result of using this inference approach for Grüneisen estimation, by showing widely varying estimations of the Grüneisen function for aluminum, depending upon whose data and whose model was employed. Segletes [10–12] has investigated the thermodynamic stability of the Grüneisen equation and has been able to place some constraints upon allowable functional behavior of the Grüneisen function. As modeling and measurement improve, such great uncertainty in the estimation of the Grüneisen parameter has and will continue to diminish.

4. THE MODEL

The currently offered model is not derived from first principles but was developed based on certain functional relationships observed in the UCC model of the cold curve. Though able to effectively match the zero-degree results of the UCC model, the current model is not, in fact, an augmented UCC model. It is, rather, a complete equation of state,

consistent with the Grüneisen constraint. By comparison, the UCC model comprises an empirical fit to the zero-degree isotherm, expressed in terms of a nondimensional lattice spacing. It embodies mechanical rather than thermodynamic concepts.

Since p_{ref} , E_{ref} and ψ are functions of volume alone, the solution to the Grüneisen equation of state [eqn. (8)] amounts to determining ψ and $G(V)$, which satisfy

$$p\psi - E = G(V) \quad . \quad (9)$$

Along the cold curve, where $p_c = -E'_c$, one obtains the differential equation

$$\psi E'_c + E_c = -G(V) \quad . \quad (10)$$

The complementary solution to eqn. (10), corresponding to $G(V) = 0$, is

$$E_c = C\Theta \quad , \quad (11)$$

which may be verified through the use of eqn. (7), where C is an integration constant.

Incidentally, it is this complementary solution that constitutes the cold curve in both the Einstein and the Debye equations of state (*i.e.*, no particular solutions were offered). But if E_c involves terms in Θ , it is not unreasonable to expect the same of $G(V)$. A particular solution to the equation

$$\psi y' + y = \Theta \quad (12)$$

is $y(V) = -\Theta \ln \Theta$.

It was the knowledge of these facts that resulted in the inspirational leap of looking at the UCC model (eqn. [1]) and surmising that the a variable was actually a $-K \ln \Theta$ term. Such a speculation was also consistent with eqn. (2), in that the natural logarithm may, over a limited domain, be well approximated by a cube-root relation like eqn. (2). Furthermore, it was speculated that the cubic term of eqn. (1) was a higher-order correction to an incorrect functional form and that it would not be needed if the logarithm were the correct form. Such a speculation could only have originated out of ignorance, of course, when it was realized that the UCC model fits data out to $a = 8$, where the cubic term carries three times the weight of the linear term. As a side note, it was later realized that Vinet *et al.* [2, 3] dropped the cubic term of Rose *et al.* from their formulation as well, since it complicated the simplicity of the form, and was not particularly important in compression. In their case, however, the resulting simplification does adversely affect the quality of their fit to binding energy in the tensile region. As is seen later, such is not the case here, since the use of the logarithmic term does, in fact, compensate for the loss of the cubic term.

Combining these hypotheses yields

$$E_c = E_b [1 - (1 + f) \exp(-f)] \quad , \quad (13)$$

where

$$f = -K \ln(\Theta/\Theta_0) \quad . \quad (14)$$

Substituting for f gives the cold energy, and the negative of its volume-derivative gives the cold pressure, as

$$E_c = E_b \left[1 - (1 - K \ln(\Theta/\Theta_0)) (\Theta/\Theta_0)^K \right] \quad (15)$$

and

$$p_c = \frac{E_b K^2}{\psi} (\Theta/\Theta_0)^K \ln(\Theta/\Theta_0) . \quad (16)$$

The general equation of state that results is obtained, using this cold curve as the reference in eqn (8), to get

$$p \psi - E = E_b \left\{ \left[(\Theta/\Theta_0)^K - 1 \right] + K (K - 1) (\Theta/\Theta_0)^K \ln(\Theta/\Theta_0) \right\} . \quad (17)$$

It can be seen that eqn (17) becomes greatly idealized if and when the parameter K takes on a value of unity. In order to satisfy the ambient sound speed condition, the constant K must take on a value of

$$K = \frac{C_0}{\Gamma_0 \sqrt{E_b}} , \quad (18)$$

which incidentally is $1/(3\Gamma_0)$ times the anharmonicity factor, η , of Rose *et al.* [1] It is shown later that values of K for real metals do, in fact, cluster in the vicinity of unity. As such, the

deviation of K from unity tells something about the nonidealness of the material. Eqns. (17) and (18) constitute the proposed equation of state, with eqns. (15) and (16) defining the associated cold curve. All that is required at this point is a specification of (Θ/Θ_0) as a function of volume.

5. A USEFUL SIMPLIFICATION

Segletes [10–12] has examined the thermodynamic stability (and instability) associated with various functional forms of the Grüneisen parameter. He proposed a form that could be made not to violate the stability metrics that he examined at the time. He expressed the form, in terms of parameter β , as

$$\Gamma = \frac{\Gamma_0}{1 + \beta\mu} . \quad (19)$$

The family of functions that satisfy this form may be simply expressed another way, in terms of the ψ variable, as

$$\psi'' = 0 . \quad (20)$$

Assuming that this form can adequately characterize metals over some relevant domain of specific volumes, we may then employ it to help us define our needed function (Θ/Θ_0) . As was shown when solving eqn. (7) for various Grüneisen forms, the effect of assuming the validity of eqn. (20) provides us with the needed relationship

$$\Theta \psi^{(1/\psi')} = \text{constant} , \quad (21)$$

keeping in mind that ψ' and thus the exponent are constants. Thus, we have

$$\Theta/\Theta_0 = (\psi/\psi_0)^{-1/\psi'} , \quad (22)$$

where ψ is linear in V , as dictated by the assumption of eqn. (20). Expressing the proposed cold curve in light of eqn. (22) yields

$$E_c = E_b \left\{ 1 - \left[1 + (K/\psi') \ln(\psi/\psi_0) \right] (\psi/\psi_0)^{(-K/\psi')} \right\} \quad (23)$$

and

$$p_c = - \frac{E_b K^2}{\psi \psi'} (\psi/\psi_0)^{(-K/\psi')} \ln(\psi/\psi_0) . \quad (24)$$

The equation of state becomes

$$p \psi - E = E_b \left\{ \left[(\psi/\psi_0)^{(-K/\psi')} - 1 \right] - (K/\psi') (K-1) (\psi/\psi_0)^{(-K/\psi')} \ln(\psi/\psi_0) \right\} . \quad (25)$$

6. COMPARISON TO THE UCC MODEL

Rose *et al.* [1] were able to express their relationship for the cold energy in terms of parameter a , which, in turn, is expressible in terms of the anharmonicity, η , and the relative volume, V/V_0 . The correspondence to the current model cannot be made on a one-to-one basis, as the current model has actually introduced an additional variable. The term ψ/ψ_0 ,

because of the assumed linearity of ψ , may be shown to be

$$\psi/\psi_0 = 1 - (\Gamma_0\psi') (1 - V/V_0) . \quad (26)$$

Similarly, the constant multiplier of K/ψ' in the f parameter, eqn. (14), may be re-expressed in terms of η such that f may be expressed as

$$f = \frac{\eta}{3 (\Gamma_0\psi')} \ln \left(1 - (\Gamma_0\psi') (1 - V/V_0) \right) . \quad (27)$$

Thus, given values for the two parameters η and $\Gamma_0\psi'$, the variables f [eqn. (27)] and a [eqn. (2)] may be implicitly related as a function of volume. The cold energy of the two models, eqns. (1) and (23), may then be compared as well. The $\Gamma_0\psi'$ term determines the effective rate of change of the Grüneisen parameter with volume. For $\Gamma_0\psi' = 1$, the Grüneisen parameter is a constant value of Γ_0 , while for $\Gamma_0\psi' = 0$, the Grüneisen function declines with increasing compression at its maximum thermodynamically stable rate, as determined by Segletes [11], according to the function $\Gamma_0/(1 + \mu)$. In all cases of expansion, the Grüneisen parameter asymptotes, at large expansion, to a value of $1/\psi'$. The family of Grüneisen functions determined by eqn. (20) is plotted versus specific volume in Fig. 1, with the parameter $\Gamma_0\psi'$ varying from 0 to unity in increments of 0.2.

In order to preserve the presentation appearance of the UCC model, data are plotted as $(E_c/E_b - 1)$ versus parameter a . In the first series of figures (Figs. 2a–2g), a family of curves,

for the current model, is plotted for a given anharmonicity, η , varying $\Gamma_0\psi'$ from 0 to 1, at increments of 0.2. In the second series of figures (Figs. 3a–3e), the parameter $\Gamma_0\psi'$ is specified, and the family of curves, for the current model, is generated by varying the anharmonicity between integral values of 3 and 9, which are seen to cover the full range of values noted by Rose *et al.* (most elements fall in the 4 to 6 range of anharmonicity). In all figures, the UCC model is plotted as a single heavy line. Many observations may be noted about the comparison of the UCC model with the currently proposed model. An enumerated list is given as follows:

- 1) The general shape of the cold curve for the two models is very similar in form, thereby indicating that, in the current model, the logarithmic function of f seems to compensate for the now-missing a^3 term;
- 2) From Figs. 2, the curves generated for the current model, corresponding to values for $\Gamma_0\psi'$ in the 0 to 0.4 range, match the UCC model most poorly, in both the tensile ($a > 0$) and compressive ($a < 0$) domains.
- 3) From Figs. 2b–2d, for anharmonicity ranges of 4 to 6 (87% of elements listed by Rose *et al.* [1] fall in the $\eta=3.5$ to 6.5 range), a value of $\Gamma_0\psi'$ in the 0.7 to 0.8 range matches the UCC tensile model very well (see also Figs. 3b, 3c).
- 4) From Fig. 3c, a value of $\Gamma_0\psi' = 0.8$ matches the UCC model in compression for all values of anharmonicity.

5) From Figs. 2g and 3e, the higher the level of anharmonicity, the greater the value of $\Gamma_0 \psi'$ required to match the UCC model results in tension. The best-fit value for $\Gamma_0 \psi'$ approaches unity as η increases to a value of 9.

6) From Fig. 2a, for very low values of η equal to 3, it is difficult to pick a single value of $\Gamma_0 \psi'$ that matches the UCC results in tension, the required value changing from 0.8 at small expansions to roughly 0.6 at larger expansions.

We may conclude that the simplification afforded by the assumption of eqn. (20) is justifiable for studying the behavior of model over limited domains of compression and expansion, based on the quality of the match to the UCC model. The general model, however, retains the flexibility to permit other functional forms on the Grüneisen parameter and will be explored more fully in the future.

7. COMPARISON TO DATA

The current model, incorporating the simplifying assumption of eqn. (20), has been used to study compression data for various materials. Since the current model is a full equation of state, its predictions may be compared not only for cold-curve compression, but also for other thermodynamic processes (*e.g.*, shock loading, for which ample data exists [18, 19]).

Though it can be done, the comparison intentionally avoids taking the approach of *tuning* all available parameters so as to best correlate the model to both cold and shock data for several reasons. First, it avoids the criticism of so-called "knob turning" to match data. Of course, the current model does have a single parameter, and that is the value of $\Gamma_0 \psi'$.

Secondly, it is known that the Grüneisen assumption becomes invalid at large enough pressures, and so an examination of when the current model diverges from the shock data could be used to indicate something about the range of validity of the Grüneisen assumption.

When possible, model parameters were derived directly from the molecular weights as well as the η and ΔE values given by Rose *et al.* [1]. These derived parameters include E_b and C_0 . With the addition of the handbook value for the thermal expansion coefficient, α , values for Γ_0 and K are directly obtained. Densities were set to the values from which most or all of the experimental data were obtained.

The only parameter that was subject to fitting was the value of $\Gamma_0 \psi'$, which determines the manner in which the Grüneisen function changes with volume (recall Fig. 1). This parameter was fitted not to give the best overall match to both the shock and cold-curve data. Rather, this parameter was fitted to give the best fit to the cold-curve alone. In this way, the model's Hugoniot is merely a prediction of and not an explicit fit to the Hugoniot data. This distinction is important, as better fits to the aggregate cold/Hugoniot data are obtainable by varying values of C_0 and Γ_0 within previously published ranges.

The model data are collected in Table 1. The parameter W is simply the molecular weight, and is used for converting molal quantities to a specific (*i.e.*, per-mass) basis. The second to last column, $\Gamma_0 \psi'$, is the only free parameter. Its value reflects the best fit to the cold-curve data. In the last column, ψ' , which is also dimensionless, is derived from other column data and is provided for informational purposes only. Graphical results are shown in Figs. 4–12 for a variety of metals. The lower curve is the fitted cold pressure curve. The upper curve (when present) is the predicted Hugoniot curve. Cold data (including theoretical predictions thereof) depicted in the figures came from Mao *et al.* [22], or were digitized from

the graphs of Rose *et al.* [1] and Molodets [23]. All shock data, against which the model predictions were compared, were taken from the Livermore compendium [18], the Kohn compilation [19], or Mitchell *et al.* [24]. All cold data are depicted with solid-filled circular symbols. All other (unfilled) symbols represent Hugoniot data.

Table 1. Model Parameters

	ρ_0 (kg/m ³)	W (g/mol)	η	E_b [†] (MJ/kg)	C_0 [§] (m/s)	α^+ (x10 ⁶) (°C ⁻¹)	Γ_0 ^{††}	K ^{‡‡}	$\Gamma_0 \psi'$	ψ'
Ag	10490	107.868	5.94	2.647	3221	19.0	2.55	0.78	0.84	0.33
Al	2700	26.982	4.71	11.939	5424	25.0	2.39	0.66	0.81	0.34
Cu	8930	63.546	5.20	5.312	3995	16.6	2.02	0.86	0.78	0.39
Li	537	6.941	3.10	22.928	4948	-	-	-	0.81	-
Mo	10200	95.94	5.85	6.846	5102	5.0	1.50	1.30	0.43	0.29
Pd	12020	106.4	6.41	3.568	4036	11.7	2.44	0.88	0.61	0.25
Pt	21430	195.09	6.47	2.893	3515	9.0	2.61	0.79	0.78	0.30
Rb	1530	85.47	4.18	0.968	1371	-	-	-	0.88	-
304 St. [¶]	7896	56.05	5.24	7.342	4733	12.0	1.81	0.97	0.76	0.42

[†] E_b calculated from ΔE values of Rose *et al.* [1] using $E_b(\text{MJ/kg}) = 96.45 \Delta E(\text{eV})/W$.

[§] C_0 calculated using eqn. (3) and values of η given by Rose *et al.* [1], rather than handbook values. Platinum is the exception, where the value of 3668 m/s yielded by eqn. (3) produces a fit to the cold curve that is not as good as when using the handbook value of 3515 m/s.

[‡]Values for thermal expansion coefficient taken from Weast [20], except for palladium, which was taken from Layne [21], and lithium and rubidium, which could not be located in the literature.

^{††}For consistency, initial Grüneisen values computed using $\Gamma_0 = \alpha C_0^2 W/R$, where R is the universal constant, equal to 8314 g m²/s² mol K. The values for Γ_0 are generally compatible with published values found elsewhere. Values of α for lithium and rubidium could not be located (nor could estimates of Γ_0).

^{‡‡} K calculated using eqn. (18).

[¶]Properties for 304 stainless steel calculated, per Rose *et al.* [1], using 70% Fe, 19% Cr, 11%Ni.

The fits to the cold-compression data are extremely good, with the model curve literally overlaying the data in nearly every case. For most cases, the Hugoniot predictions are very good to a point, though model results in some cases, notably silver and platinum, diverge from data at higher pressures. Lithium and rubidium are special cases, in that it does not appear possible that the cold [1] and Hugoniot [18] data were even generated from the same density base material. In particular, Hugoniot data, which should universally lie at higher pressures than the cold curve, are not seen to exceed the cold-curve data until a relative compression of approximately 2. For this reason, and the fact that thermal expansion data and Grüneisen estimates could not be obtained for the materials, no attempt was even made to model the lithium and rubidium Hugoniots. In the case of aluminum, the poor fit at even moderate pressures is perhaps attributable to a phase change since, as shown in Figure 5 with the dotted curve, when using an initial Grüneisen value of 1.2 (half of the value shown in Table 1), an excellent fit to the aluminum Hugoniot prevails to 9 Mbar. Such a notion is buttressed by the work of McKenna and Pastine [16], whose empirical fit to the aluminum Grüneisen function decreases with compression at such a prodigious rate (in the V/V_0 range from 1.0 to 0.85) that it violates the stability metrics of Segletes [10, 11], established for thermodynamic transitions of single-phase Grüneisen materials. Thus, if McKenna's fit is accurate, then either the aluminum Grüneisen function varies with temperature (violating the Grüneisen assumption) or else the aluminum Hugoniot experiences a phase change in V/V_0 range of 0.85 to 1.0.

Table 2 gives a very approximate estimation of the goodness of the match of the current model to the Hugoniot data, in terms of pressure, and includes, in the last column, the Debye temperature for each material. In all cases except aluminum, good matches to the Hugoniot are obtained out to pressures of approximately 1 Mbar or greater. Furthermore, the two materials, silver and platinum, that were observed to experience only fair correlations at higher pressures, happen to be the materials with notably low Debye temperatures. It is

Table 2. *Limiting Pressure Ranges (Mbar) to which Model Prediction Qualitatively Correlates with Hugoniot Data*

	Quality of Model Correlation with Hugoniot Data			Θ_D^\dagger (K)
	Excellent	Good	Fair	
Ag	0.5	0.9	1.6+	220
Al	—	0.5	0.7	380
Cu	1.2	4.2+	—	310
Mo	0.6	1.7+	—	375
Pd	0.5	2.2+	—	—
Pt	2.0	2.0	2.7+	225
304 St. Steel	1.9+	—	—	433 [*]

[†]Data extracted from Andrews [6].

^{*}Value reflects that of pure iron.

surmised that perhaps the breakdown of the Grüneisen assumption, eqn. (4), at high pressures (actually temperature) is responsible for the divergence of the model from the data. In the case of aluminum, a possible cause of the poor Hugoniot prediction has already been discussed. In line with specific heat theory and the notion of a characteristic temperature, it would seem to make proper thermodynamic sense that the breakdown of the Grüneisen assumption with temperature might also scale with the characteristic temperature [*i.e.*, the breakdown occurs as a function of (Θ/T)]. With the exception of aluminum, the results of Table 2 would seem to support this reasoning.

8. CONSTRAINTS ON THE FREE PARAMETER, $\Gamma_0 \psi'$

The free parameter in the current model, $\Gamma_0 \psi'$, obviously has physical meaning and relates to the rate of Grüneisen parameter change with volume. Ideally, it could be quantified from other physical constants. Since the characteristic temperature in the current model is always normalized by its ambient value though, one is limited in trying to extract additional information directly from this form. The assumed Grüneisen form, eqn. (20), dictates that $\Gamma_0 \psi' = 1$ be an upper limit on the model parameter. For a lower limit, stability analyses conducted by Segletes [11] showed, on the basis of high pressure isobaric transitions, that the maximum rate of descent of the Grüneisen function with compression is limited such that $\psi' \geq 0$. At cold pressures, however, a different isobaric criterion arises, in which it was shown that a stable compressive cold curve must obey the relation

$$-p'_c/p_c \geq 1/\psi \quad . \quad (28)$$

Applying this criterion to the current model gives a lower bound on the model parameter as

$$\psi' \geq \frac{1 - K}{1 - \frac{1}{\ln(\psi/\psi_0)}} \quad . \quad (29)$$

It should be immediately noted that the value of the parameter K , which equals $\eta/3\Gamma_0$, drives the lower bound on ψ' . In particular, for materials in which K is greater than unity, the high-pressure $\psi' \geq 0$ criterion is the most restrictive constraint. For K less than unity, the low-

pressure constraint, given by eqn. (29), governs the problem. For K equal to unity, both criteria coincide and the equation of state, eqn. (17), simplifies immensely, with the right-hand term identically zero and all exponents equal to unity.

Considering eqn. (29), for the worst-case compression scenerio, one may take the argument of the logarithm as $(1 - \Gamma_0 \psi')$. The results of this criterion give lower allowable limits on the model parameter, $\Gamma_0 \psi'$, below the fitted value for each of the materials studied, with minimum levels generally below the 0.4 level. This result reinforces our comparison with the UCC model, in which low values (0 to 0.4) of the model parameter did not fit the UCC model in tension well. The span from 0.4 to 1, though, still leaves a large, permissable range on the value of the parameter $\Gamma_0 \psi'$. Further analysis may serve to better define this parameter, either in terms of more restrictive limits or in terms of fundamental quantity groupings.

9. CONCLUSIONS

An equation of state for metals has been proposed. The form of the equation provides a very close match to the cold-temperature expansion models, cold-compression data, and shock-compression data. The model was inspired by the Universal Cold Curve (UCC) model of Rose *et al.* [1], when it was realized that algebraic terms in the UCC model bore a functional resemblance to thermodynamic terms that could be the solution to the Grüneisen cold curve. In the model, the cold energy is completely expressible with terms involving the material's characteristic temperature.

A simplified form of the current model has one free parameter per given material, which physically relates to the rate at which the Grüneisen parameter changes with volume.

The fitting parameter for the model is not totally free, but is constrained within certain bounds, based on considerations of thermodynamic stability. With this one parameter, excellent fits to cold curves are produced to all available low-temperature compression data, including platinum cold compressions to 6 Mbar. Once the fitting parameter is set for the cold curve, other thermodynamic paths may be predicted without the need of additional fitting parameters. The resulting predictions of Hugoniot behavior match shock-compression data well, typically to the megabar range, before diverging. The divergence of the current model with very high pressure shock data might be attributable to the breakdown of the Grüneisen assumption at high pressures.

Additional avenues remain to be explored with the current model, which include enhancing the formulation to properly account for the very high pressure regions, examining more fully the properties of the equation of state in tension, and examining the general form of the equation of state, eqn. (15). Ultimately, one seeks to understand the underlying physics of lattice compression and vibration that would lead to an equation of state of the form proposed. As it is, the current model hopefully serves to put the often-used Grüneisen equation of state on a firmer foundation.

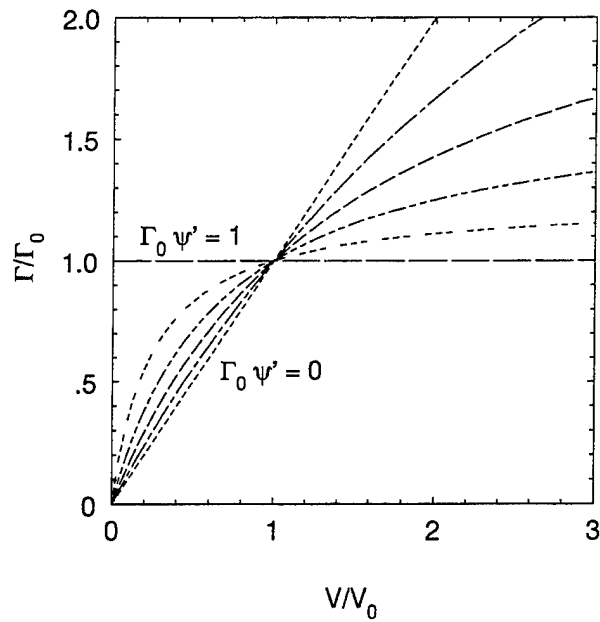


Figure 1. Relative Grüneisen parameter versus relative volume as a function of parameter $\Gamma_0 \psi'$, taken in increments of 0.2, for the assumed form $\psi'' = 0$.

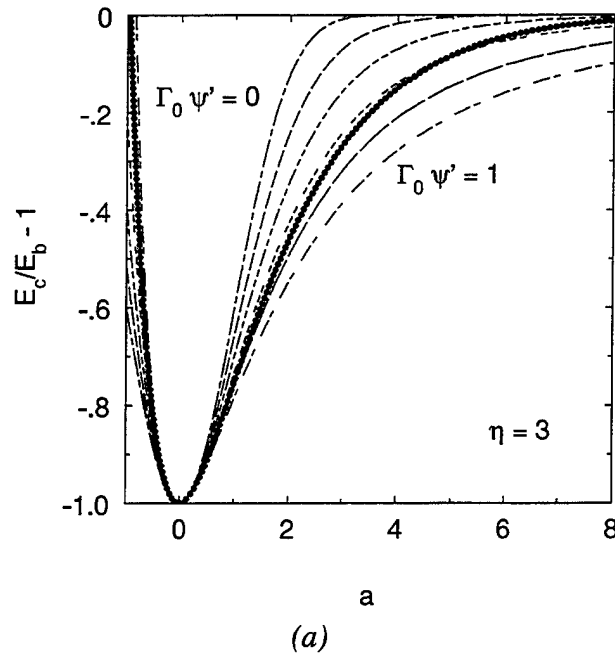


Figure 2. Comparison of binding energy of current model to that of Rose et al. [1], for given anharmonicities. Rose curve depicted with dark line. Current model shown in dashed lines for incremental values of $\Gamma_0 \psi'$, ranging from 0 to 1 in increments of 0.2. (a) $\eta = 3$. (b) $\eta = 4$. (c) $\eta = 5$. (d) $\eta = 6$. (e) $\eta = 7$. (f) $\eta = 8$. (g) $\eta = 9$.

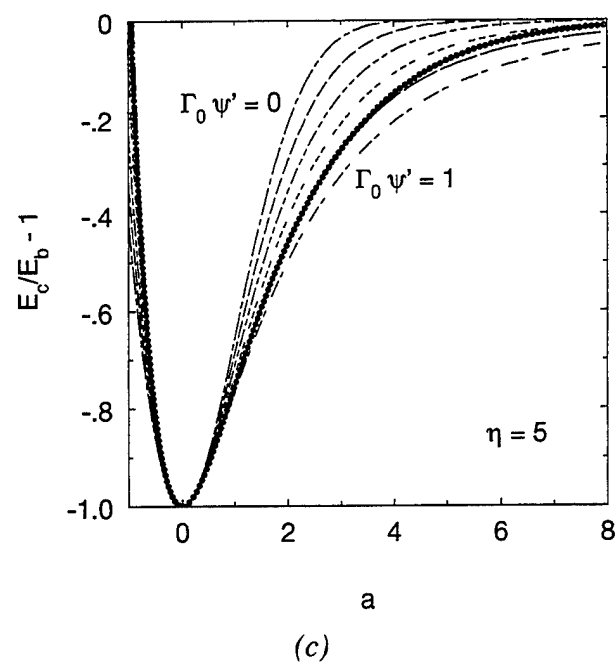
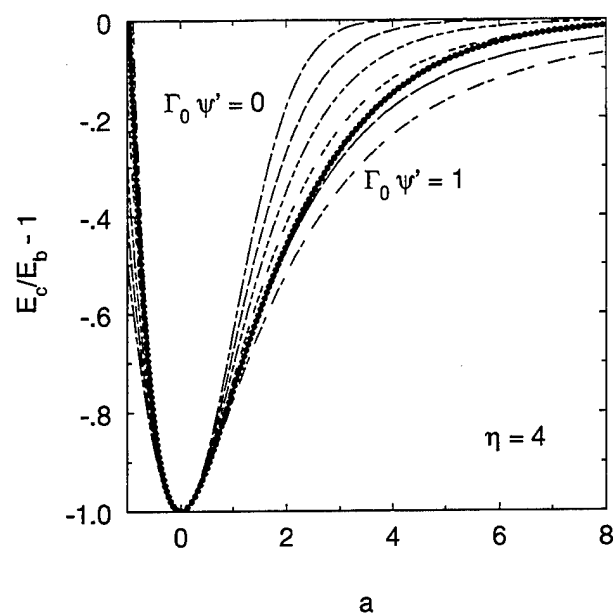


Figure 2 (continued). Comparison of binding energy of current model to that of Rose *et al.* [1], for given anharmonicities. Rose curve depicted with dark line. Current model shown in dashed lines for incremental values of $\Gamma_0 \psi'$, ranging from 0 to 1 in increments of 0.2. (a) $\eta = 3$. (b) $\eta = 4$. (c) $\eta = 5$. (d) $\eta = 6$. (e) $\eta = 7$. (f) $\eta = 8$. (g) $\eta = 9$.




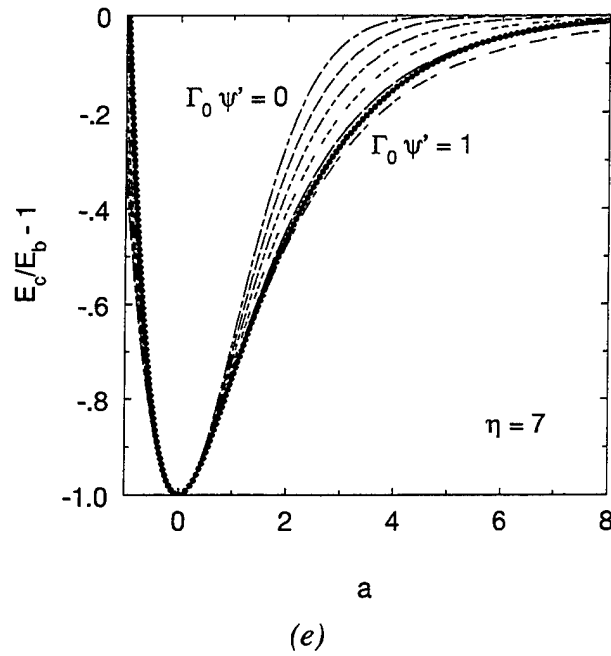


Figure 2 (continued). Comparison of binding energy of current model to that of Rose *et al.* [1], for given anharmonicities. Rose curve depicted with dark line. Current model shown in dashed lines for incremental values of $\Gamma_0 \psi'$, ranging from 0 to 1 in increments of 0.2. (a) $\eta = 3$. (b) $\eta = 4$. (c) $\eta = 5$. (d) $\eta = 6$. (e) $\eta = 7$. (f) $\eta = 8$. (g) $\eta = 9$.

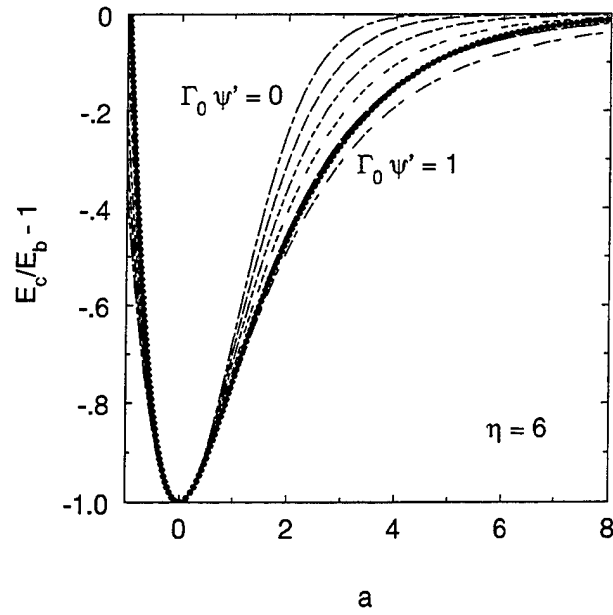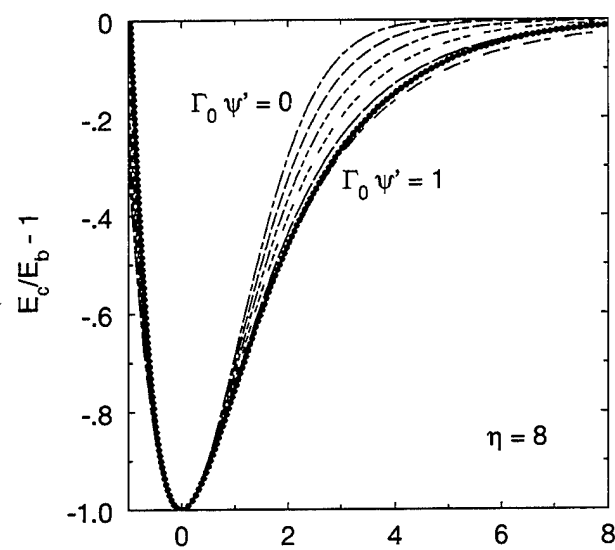

a


(f)

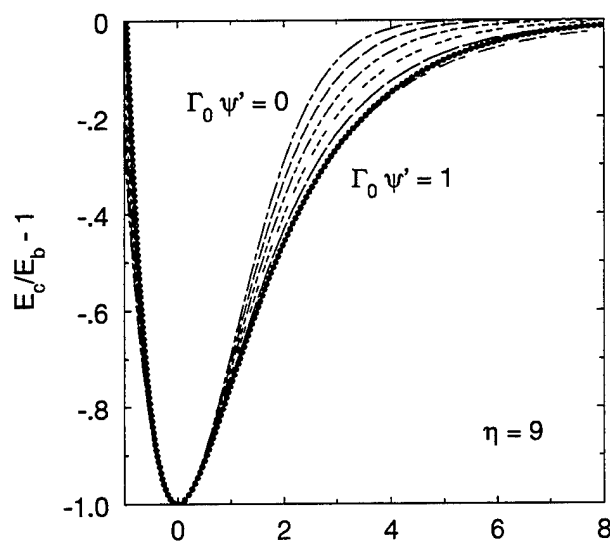


a

(g)

Figure 2 (continued). Comparison of binding energy of current model to that of Rose *et al.* [1], for given anharmonicities. Rose curve depicted with dark line. Current model shown in dashed lines for incremental values of $\Gamma_0 \psi'$, ranging from 0 to 1 in increments of 0.2. (a) $\eta = 3$. (b) $\eta = 4$. (c) $\eta = 5$. (d) $\eta = 6$. (e) $\eta = 7$. (f) $\eta = 8$. (g) $\eta = 9$.

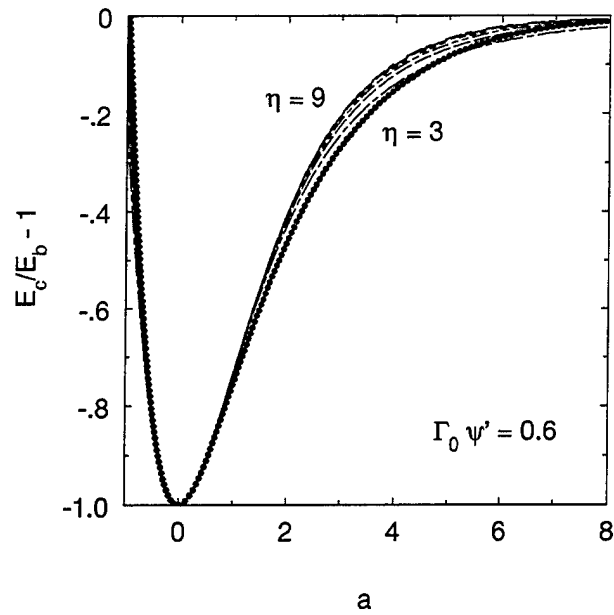


(a)

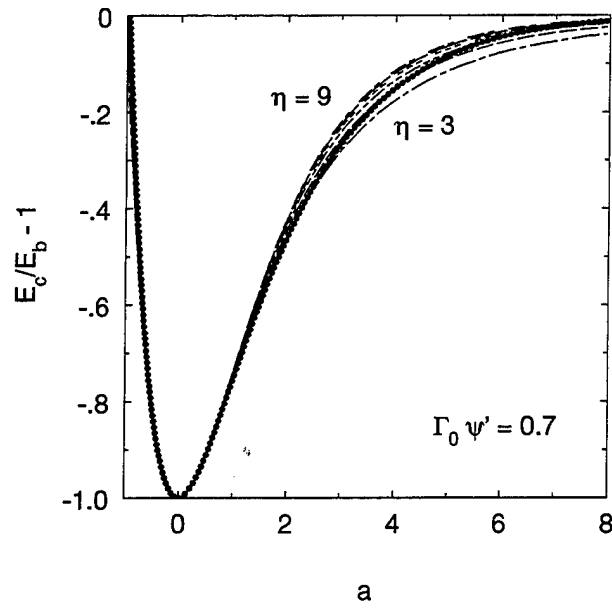


(b)

Figure 3. Comparison of binding energy of the current model to that of Rose et al. [1], for given values of $\Gamma_0 \psi'$ parameter. Rose curve depicted with dark line. Current model shown in dashed lines for integral values of η , ranging from 3 to 9.

(a) $\Gamma_0 \psi' = 0.6$. (b) $\Gamma_0 \psi' = 0.7$. (c) $\Gamma_0 \psi' = 0.8$. (d) $\Gamma_0 \psi' = 0.9$. (e) $\Gamma_0 \psi' = 1.0$.

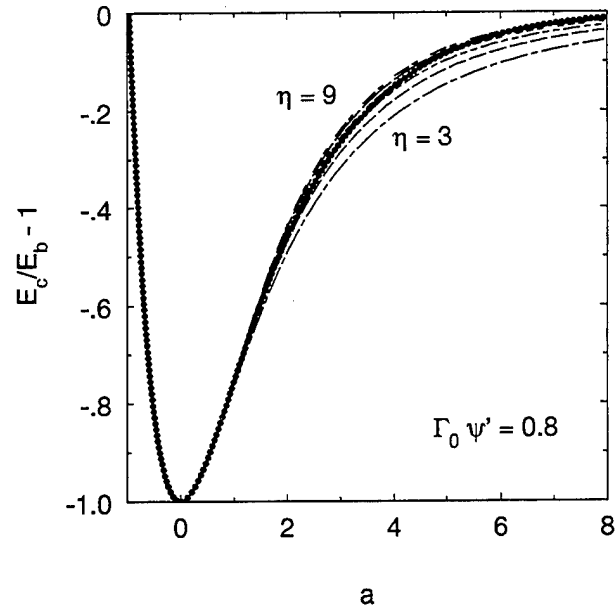


(c)

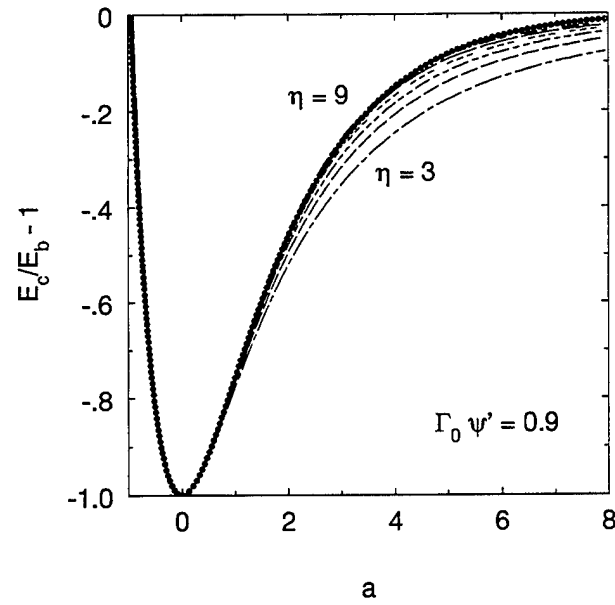

(d)

Figure 3 (continued). Comparison of binding energy of the current model to that of Rose *et al.* [1], for given values of $\Gamma_0 \psi'$ parameter. Rose curve depicted with dark line. Current model shown in dashed lines for integral values of η , ranging from 3 to 9. (a) $\Gamma_0 \psi' = 0.6$. (b) $\Gamma_0 \psi' = 0.7$. (c) $\Gamma_0 \psi' = 0.8$. (d) $\Gamma_0 \psi' = 0.9$. (e) $\Gamma_0 \psi' = 1.0$.

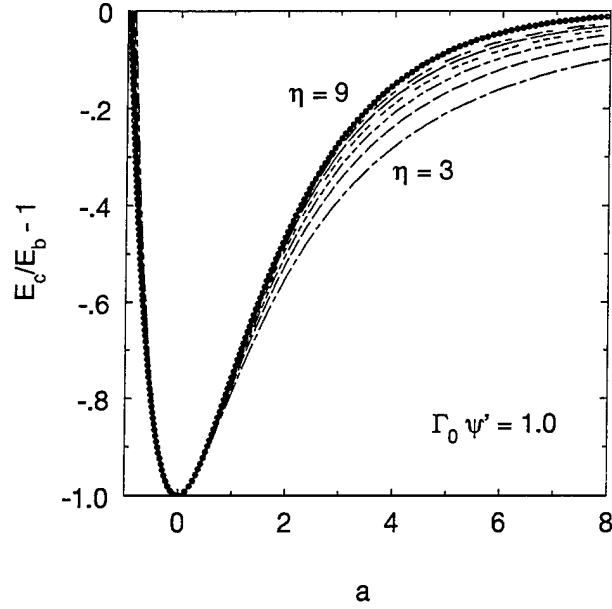

(e)

Figure 3 (continued). Comparison of binding energy of the current model to that of Rose et al. [1], for given values of $\Gamma_0 \psi'$ parameter. Rose curve depicted with dark line. Current model shown in dashed lines for integral values of η , ranging from 3 to 9. (a) $\Gamma_0 \psi' = 0.6$. (b) $\Gamma_0 \psi' = 0.7$. (c) $\Gamma_0 \psi' = 0.8$. (d) $\Gamma_0 \psi' = 0.9$. (e) $\Gamma_0 \psi' = 1.0$.

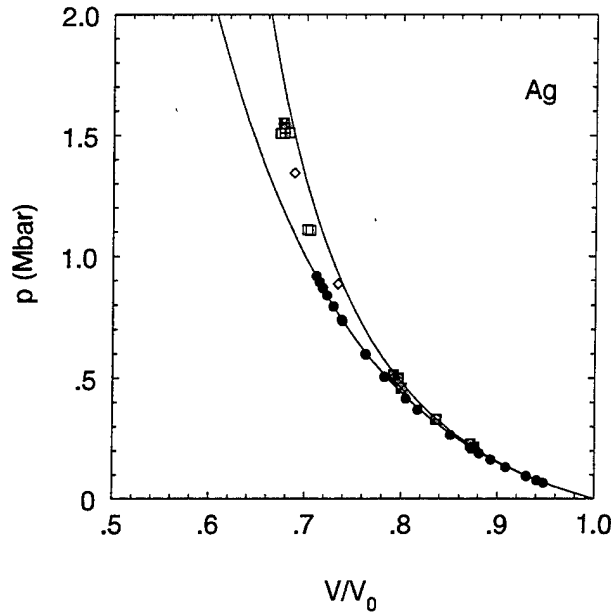


Figure 4. Cold-curve fit with Hugoniot prediction for silver, to 2 Mbar. Cold data [22] (filled symbols) and Hugoniot data [18, 19] (unfilled symbols) included.

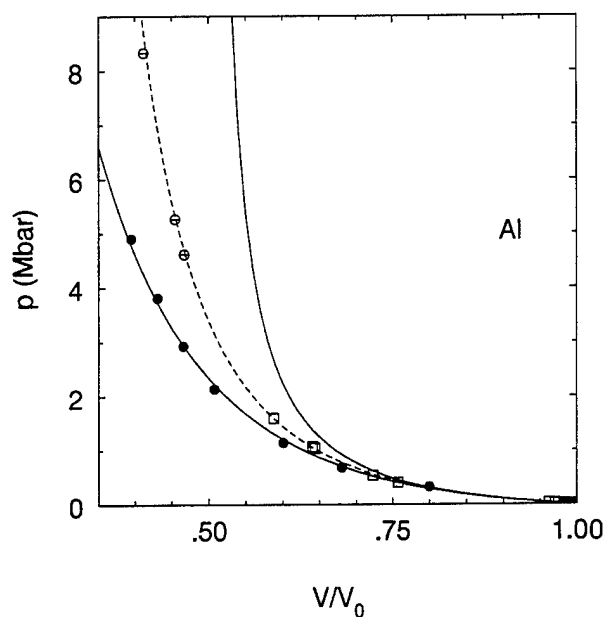


Figure 5. Cold-curve fit with Hugoniot prediction for aluminum, to 9 Mbar. Cold data [23] (filled symbols) and Hugoniot data [19, 24] (unfilled symbols) included. Dashed curve is Hugoniot prediction, assuming $\Gamma_0 = 1.2$.

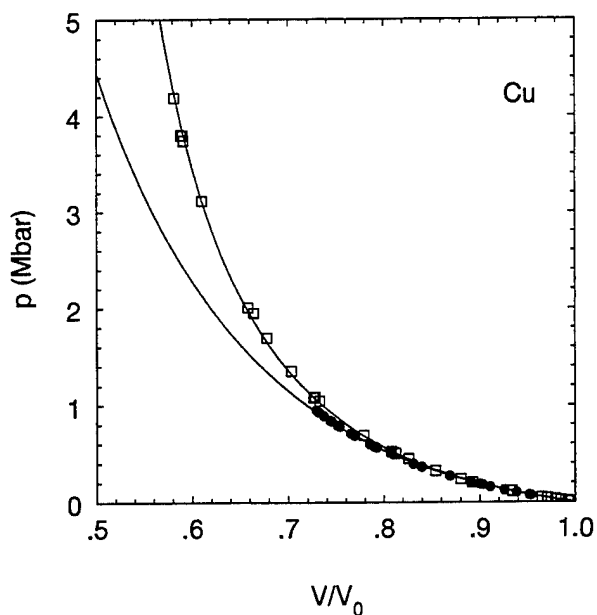


Figure 6. Cold-curve fit with Hugoniot prediction for copper, to 5 Mbar. Cold data [22] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.

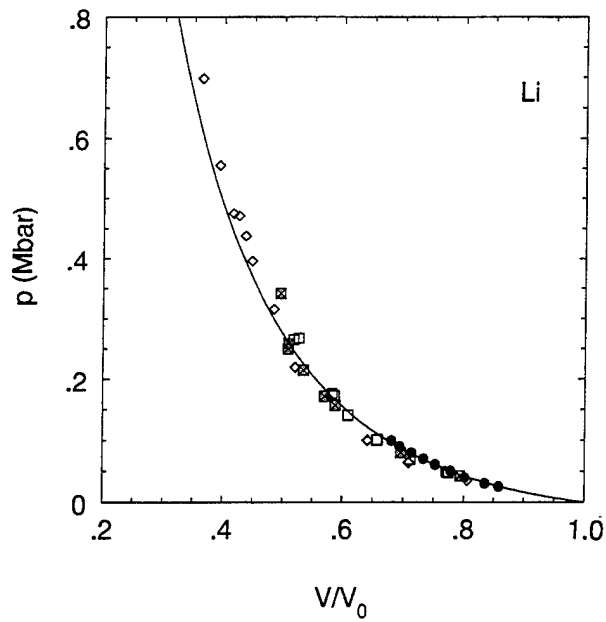


Figure 7. Cold-curve fit for lithium, to 0.8 Mbar. Cold data [1] (filled symbols) and Hugoniot data [18] (unfilled symbols) included.

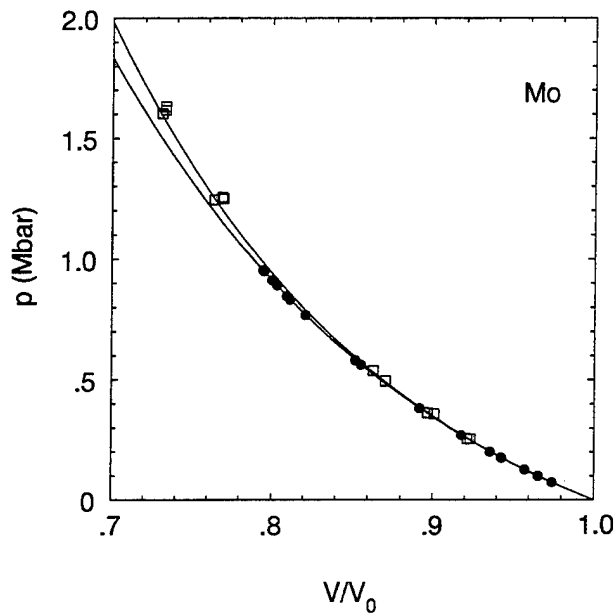


Figure 8. Cold-curve fit with Hugoniot prediction for molybdenum, to 2 Mbar. Cold data [22] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.

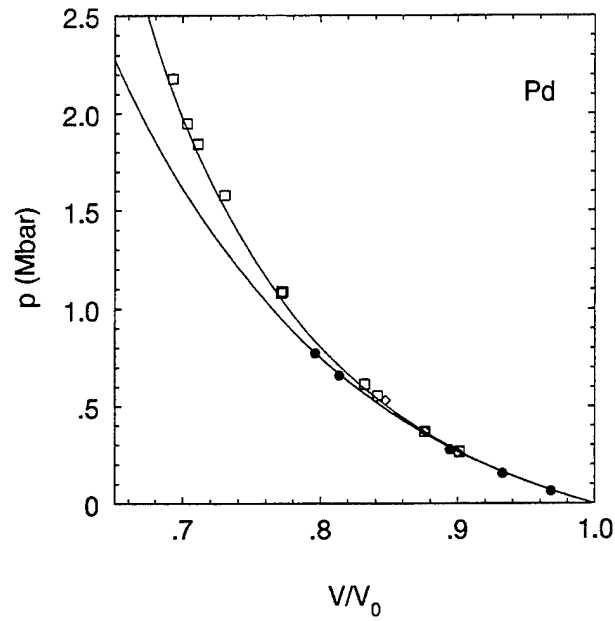


Figure 9. Cold-curve fit with Hugoniot prediction for palladium, to 2.5 Mbar. Cold data [22] (filled symbols) and Hugoniot data [18] (unfilled symbols) included.

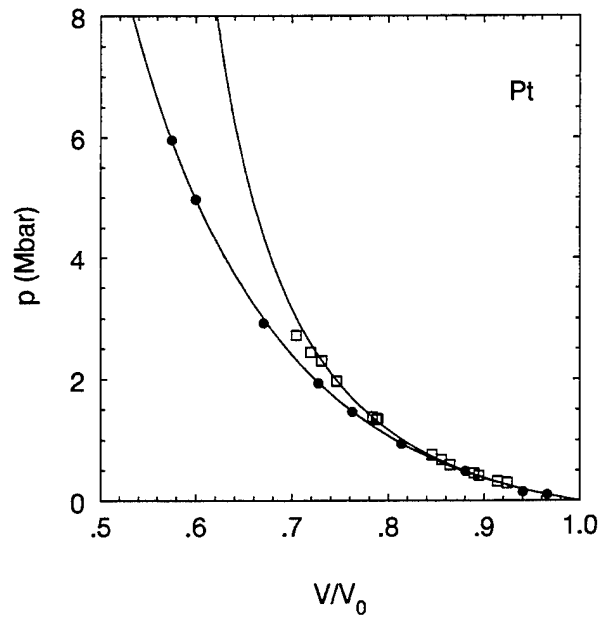


Figure 10. Cold-curve fit with Hugoniot prediction for platinum, to 8 Mbar. Cold data [1] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.

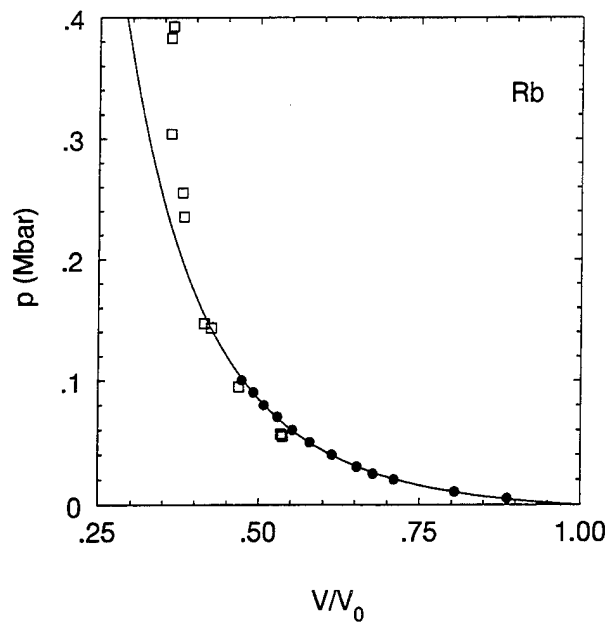


Figure 11. Cold-curve fit for rubidium, to 0.4 Mbar. Cold data [1] (filled symbols) and Hugoniot data [18] (unfilled symbols) included.

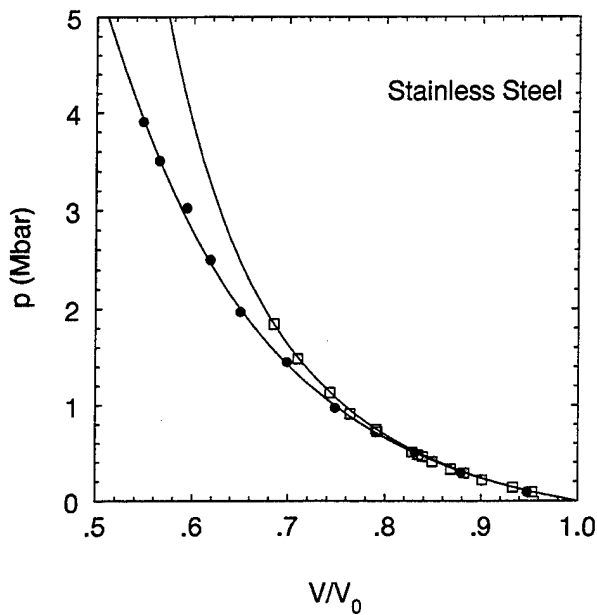


Figure 12. Cold-curve fit with Hugoniot prediction for 304 stainless steel (70% Fe, 19% Cr, 11% Ni), to 5 Mbar. Cold data [1] (filled symbols) and Hugoniot data [19] (unfilled symbols) included.

10. REFERENCES

1. Rose, J.H., J.R. Smith, F. Guinea, and J. Ferrante. "Universal Features of the Equation of State of Metals." *Physical Review B*, **29** (6), pp. 2963–2969, 1984.
2. Vinet, P., J.R. Smith, J. Ferrante, and J.H. Rose. "Temperature Effects on the Universal Equation of State for Solids." *Physical Review B*, **35** (4), pp. 1945–1953, 1987.
3. Vinet, P., J.H. Rose, J. Ferrante, and J.R. Smith. "Universal Features of the Equation of State of Solids." *Journal of Physics: Condensed Matter*, **1**, pp. 1941–1963, 1989.
4. Baonza, V.G., M. Cáceres, and J. Núñez. "Universal Compressibility Behavior of Dense Phases." *Physical Review B*, **51** (1), pp. 28–37, 1995.
5. Baonza, V.G., M. Taravillo, M. Cáceres, and J. Núñez. "Universal Features of the Equation of State of Solids from a Pseudospinodal Hypothesis." *Physical Review B*, **53** (9), pp. 5252–5258, 1996.
6. Andrews, F.C. *Equilibrium Statistical Mechanics*. John Wiley: New York, 1963.
7. Desloge, E.A. *Thermal Physics*. Holt, Rinehart & Winston: New York, 1968.
8. Slater, J.C. *Introduction to Chemical Physics*. McGraw Hill: New York, 1939.
9. Grodzka, P.G. "Grüneisen Parameter Study." Lockheed Missile Space Company Report LMSC/HREC A784868, Huntsville, AL, 1967.
10. Segletes, S.B. "Further Examinations on the Thermodynamic Stability of the Mie-Grüneisen Equation of State." *Journal of Applied Physics*, **76** (8), pp. 4560–4566, 1994.
11. Segletes, S.B. "The Effect of Thermodynamic Constraints upon the Mie-Grüneisen Equation of State" in *Constitutive Laws*. A.M. Rajendran, R.C. Batra (eds.), CIMNE: Barcelona, pp. 46–51, 1995.

12. Segletes, S.B. "Thermodynamic Stability of the Mie-Grüneisen Equation of State, and Its Relevance to Hydrocode Computations." *Journal of Applied Physics*, **70** (5), pp. 2489–2499, 1991. Erratum: **71** (2), p. 1074.
13. Kerley, G.I. "User Manual for PANDA II: A Computer Code for Calculating Equations of State." Sandia Laboratories Report SAND88–2291, Albuquerque, NM, July, 1991.
14. Walsh, J.M., M.H. Rice, R.G. McQueen, and F.L. Yarger. "Shock-Wave Compressions of Twenty-Seven Metals. Equations of State of Metals." *Physical Review*, **108** (2), pp. 196–216, 1957.
15. McQueen, R.G., and S.P. Marsh. "Equation of State for Nineteen Metallic Elements from Shock-Wave Measurements to Two Megabars." *Journal of Applied Physics*, **31** (7), pp. 1253–1269, 1960.
16. McKenna, P., and D.J. Pastine. "Volume Dependence of the Grüneisen Parameter for Aluminum." *Journal of Applied Physics*, **39** (13), p. 6104, 1968.
17. Dugdale, J.S., and D.K.C. McDonald. "The Thermal Expansion of Solids." *Physical Review*, **89** (4), pp. 832–834, 1953.
18. van Thiel, M., A.S. Kusibov, and A.C. Mitchell (eds.). "Lawrence Radiation Laboratory Compendium of Shock Wave Data." UCRL–50108, University of California, Livermore, CA, 1967.
19. Kohn, B.J. "Compilation of Hugoniot Equations of State." AFWL–TR–69–38, U.S. Air Force Weapons Laboratory, Kirtland AFB, NM, April, 1969.
20. Weast, R.C. (ed.). *Handbook of Chemistry and Physics*. CRC: Cleveland, 1975.
21. Layne, A.A. (ed.). "Materials Selector Issue." *Materials Engineering*, **70** (5), p. 140, 1969.

22. Mao, H.K., P.M. Bell, J.W. Shaner, and D.J. Steinberg. "Specific Volume Measurements of Cu, Mo, Pd, and Ag and Calibration of the Ruby R₁ Fluorescence Pressure Gauge From 0.06 to 1 Mbar." *Journal of Applied Physics*, **49** (6), pp. 3276–3283, 1978.
23. Molodets, A.M. "Grüneisen Function and the Zero-Temperature Isotherm of Three Metals up to Pressures of 10 TPa." *JETP*, **80** (3), pp. 467–471, 1995.
24. Mitchell, A.C., W.J. Nellis, J.A. Moriarty, R.A. Heinle, N.C. Holmes, R.E. Tipton, and G.W. Repp. "Equation of State of Al, Cu, Mo, and Pb at Shock Pressures up to 2.4 TPa (24 Mbar)." *Journal of Applied Physics*, **69** (5), pp. 2981–2986, 1991.

INTENTIONALLY LEFT BLANK

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFO CTR ATTN DTIC DDA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218
1	HQDA DAMO FDQ ATTN DENNIS SCHMIDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460
1	US MILITARY ACADEMY MATH SCI CTR OF EXCELLENCE DEPT OF MATHEMATICAL SCI ATTN MDN A MAJ DON ENGEN THAYER HALL WEST POINT NY 10996-1786
1	DIRECTOR US ARMY RESEARCH LAB ATTN AMSRL CS AL TP 2800 POWDER MILL RD ADELPHI MD 20783-1145
1	DIRECTOR US ARMY RESEARCH LAB ATTN AMSRL CS AL TA 2800 POWDER MILL RD ADELPHI MD 20783-1145
3	DIRECTOR US ARMY RESEARCH LAB ATTN AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1145
	<u>ABERDEEN PROVING GROUND</u>
2	DIR USARL ATTN AMSRL CI LP (305)

NO. OF COPIES	ORGANIZATION
1	US ARMY DUSA OPS RSCH ATTN DANIEL WILLARD 102 ARMY PENTAGON WASHINGTON DC 20310-0102
1	ARMY SCIENCE BD WASH DC ATTN RICHARD L HALEY 2501 DUXBURY PLACE ALEXANDRIA VA 22308
1	ARMY SCIENCE BOARD ORNL HEALTH SCI RSCH DIV ATTN ANETTA P WATSON BLDG 45005 MS 6101 OAK RIDGE TN 37831-6101
1	MIT LINCOLN LAB ARMY SCIENCE BOARD ATTN WADE M KORNEGAY 244 WOOD ST RM S2 139 LEXINGTON MA 02173
5	DEFENSE NUCLEAR AGENCY ATTN MAJ JAMES LYON CDR KENNETH W HUNTER TONY FREDERICKSON R JEFFREY LAWRENCE SPSP KIM KIBONG 6801 TELEGRAPH RD ALEXANDRIA VA 22310-3398
3	COMMANDER US ARMY ARDEC ATTN AMSTA AR FSA E W P DUNN J PEARSON E BAKER PICATINNY ARSENAL NJ 07806-5000
1	COMMANDER US ARMY ARDEC ATTN AMSTA AR CCH V M D NICOLICH PICATINNY ARSENAL NJ 07806-5000
1	COMMANDER US ARMY ARDEC ATTN E ANDRICOPOULOS PICATINNY ARSENAL NJ 07806-5000

NO. OF COPIES	ORGANIZATION
1	COMMANDER USA STRATEGIC DEFNS CMD ATTN CSSD H LL T CROWLES HUNTSVILLE AL 35807-3801
2	COMMANDER US ARMY MICOM ATTN AMSMI RD ST WF D LOVELACE M SCHEXNAYDER REDSTONE ARSENAL AL 35898-5250
1	MIS DEFNS & SPACE TECHNOLOGY ATTN CSSD SD T KENNETH H JORDAN PO BOX 1500 HUNTSVILLE AL 34807-3801
4	COMMANDER US ARMY BEL VOIR RD&E CTR ATTN STRBE NAE B WESTLICH STRBE JMC T HANSHAW STRBE NAN S G BISHOP J WILLIAMS FORT BEL VOIR VA 22060-5166
3	COMMANDER US ARMY RESEARCH OFFICE ATTN J CHANDRA K IYER J BAILEY PO BOX 12211 RESEARCH TRIANGLE PARK NC 27709-2211
1	NAVAL RESEARCH LABORATORY ATTN ANDREW E WILLIAMS CODE 6684 4555 OVERLOOK AVE SW WASHINGTON DC 20375
1	NAVAL AIR WARFARE CTR ATTN STEPHEN A FINNEGAN BOX 1018 RIDGECREST CA 93556
3	COMMANDER NAVAL WEAPONS CENTER ATTN T T YEE CODE 3263 D THOMPSON CODE 3268 W J MCCARTER CODE 6214 CHINA LAKE CA 93555

NO. OF COPIES	ORGANIZATION
9	<p>COMMANDER NAVAL SURFACE WARFARE CTR DAHLGREN DIVISION ATTN C R GARRETT CODE G22 W HOLT CODE G22 CHARLES R ELLINGTON W WALLACE MORTON JR JOHN M NELSON WILLIAM J STROTHER D L DICKINSON CODE G24 L F WILLIAMS CODE G33 M J SILL CODE H11 17320 DAHLGREN RD DAHLGREN VA 22448-5000</p>
13	<p>COMMANDER NAVAL SURFACE WARFARE CTR ATTN D TASKER CODE 9220 W WILSON P C HUANG CODE G402 B A BAUDLER CODE R12 R H MOFFETT CODE R12 R GARRETT CODE R12 T L JUNGLING CODE R32 R DAMINITY CODE U43 J P MATRA P WALTER L MENSI K KIDDY F J ZERILLI 10901 NEW HAMPSHIRE AVE SILVER SPRING MD 20903-5000</p>
1	<p>DIRECTOR NAVAL CIVIL ENGRNG LAB ATTN J YOUNG CODE L56 PORT HUENEME CA 93043</p>
1	<p>NAVAL POST GRADUATE SCHOOL PHYSICS DEPARTMENT ATTN JOSEPH STERNBERG MONTEREY CA 93943</p>

NO. OF COPIES	ORGANIZATION
5	<p>AIR FORCE ARMAMENT LAB ATTN AFATL DLJW W COOK M NIXON AFATL DLJR J FOSTER AFATL MNW LT D LOREY R D GUBA EGLIN AFB FL 32542</p>
5	<p>WRIGHT LABS ATTN MNMW JOEL W HOUSE ARMAMENT DIRECTORATE STE 326 B1 RONALD D HUNT BRYAN MILLIGAN BRUCE C PATTERSON WADE H VAUGHT 101 W EGLIN BLVD EGLIN AFB FL 32542-6810</p>
2	<p>USAF PHILLIPS LABORATORY ATTN PL WSCD FIROOZ ALLAHDAI PV VTA DAVID SPENCER 3550 ABERDEEN AVE SE KIRTLAND AFB NM 87117-5776</p>
1	<p>USAF PHILLIPS LABORATORY VTSI ATTN ROBERT ROYBAL KIRTLAND AFB NM 87117-7345</p>
1	<p>AFIT ENC ATTN DAVID A FULK WRIGHT PATTERSON AFB OH 45433</p>
1	<p>US DEPT OF ENERGY IDAHO OPERATIONS OFFICE ATTN RONALD H JOHNSON 850 ENERGY DR IDAHO FALLS ID 83401-1563</p>

NO. OF COPIES	ORGANIZATION
44	DIRECTOR SANDIA NATL LABS ATTN E S HERTEL JR MS 0819 L N KMETYK E H BARSIS MS 031 ERIC W REECE MS 0307 DANIEL P KELLY MS 0307 L WEIRICK MS 0327 R TACHAU MS 0425 D LONGCOPE MS 0439 R REEDER D HAYES MS 0457 J ASAY MS 0458 W TEDESCHI MS 0482 J SCHULZE MS 0483 J SOUTHWARD PAUL A LONGMIRE MS 0560 T TRUCANO MS 0819 J MICHAEL MCGLAUN MS 0819 R BRANNON MS 0820 J ANG MS 0821 M BOSLOUGH MS 0821 L CHHABILDAS MS 0821 D CRAWFORD MS 0821 J DICK M FURNISH MS 0821 C HALL MS 0821 W REINHART MS 0821 P STANTON MS 0821 P TAYLOR ORG 1432 D KERNAN ORG 1433 C KONRAD K LANG M KIPP DIV 1533 A ROBINSON DIV 1533 P YARRINGTON DIV 1533 J MCGLAWA DIV 1541 M FORRESTAL DIV 1551 R GRAHAM DIV 1551 R LAFARGE DIV 1551 C HILLS DIV 1822 W J ANDRZEJEWSKI DIV 2512 D MARCHI DIV 2512 W VANDERMOLLEN ORG 2653 B LEVIN ORG 7816 R O NELLUMS DIV 9122 PO BOX 5800 ALBUQUERQUE NM 87185-0307

NO. OF COPIES	ORGANIZATION
3	DIRECTOR LLNL ATTN JOSEPH V REPA MS A133 MICHAEL O SCHNICK MS F607 EDWARD J CHAPYAK MS F664 PO BOX 1663 LOS ALAMOS NM 87545
33	DIRECTOR LLNL ATTN R E TIPTON L35 D BAUM L35 T MCABEE MS 35 M J MURPHY R PIERCE L122 R ROSINKY L122 O J ALFORD L122 D STEWART L122 T VIDLAK L122 B R BOWMAN L122 W DIXON L122 A C MITCHELL J A MORIARTY R A HEINLE N C HOLMES R PERRET L163 W SHOTTS L163 H KRUGER L178 G POMYKAL L178 M SHANNON G SIMONSON L180 A SPERO L180 W TAO L282 P URTIEW L282 A HOLT L290 J E REAUGH L290 W J NELLIS L299 D WOOD L352 D GAVEL L495 J HUNTER L495 E JOHANSSON L495 R M KUKLO L874 G W REPP PO BOX 808 LIVERMORE CA 94550

NO. OF
COPIES ORGANIZATION

8 DIRECTOR
LLNL
ATTN DOUGLAS R FAUX L125
NORMAN W KLINO L125H
ROBERT BARKER L159
MILTON FINGER L163
MICHAEL GERASSIMENKO L178
FRANK A HANDLER L182
STEPHEN G COCHRAN L389
BMDO ROBERT M HALL
PO BOX 808
LIVERMORE CA 94551-0808

34 DIRECTOR
LANL
ATTN M LUCERO MS A105
D MANDELL
K MARK
J P RITCHIE MS B214 T14
R DINGUS MS B218
N KRIKORIAN MS B228
R KIRKPATRICK MS B229
R THURSTON MS B229
C T KLINGNER MS B294
R MILLER MS B294
S J MOSSO
B SHAFER MS C931
G GISLER MS D436
C RAGAN MS D449
B LAUBSCHER MS D460
R WELLS MS F607
R KOPP MS F645
R STELLINGWERF MS F645
C WINGATE MS F645
T ADAMS MS F663
R GODWIN MS F663
K JACOBY MS F663
W SPARKS MS F663
J SHANER MS F670
G CANAVAN MS F675
R GREINER MS G740
J HILLS MS G770
B HOGAN MS G770
J BOLSTAD MS G787
J WALSH MS G787
R DAVIDSON MS K557
R HENNINGER MS K557 N6
T ROLLET MS K574
W DEAL MS P915
PO BOX 1663
LOS ALAMOS NM 87545

NO. OF
COPIES ORGANIZATION

12 DIRECTOR
LANL
ATTN P HOWE MS P915
J KENNEDY MS P915
A ROACH MS P915
L SCHWALBE
W HEMSING MS P940
R KARPP MS P940
E POGUE MS P940
J MCAFEE MS P950
D PAISLEY MS P950
L PICKLESIMER MS P950
R WARNES MS P950
S SHEFFIELD MS P952
PO BOX 1663
LOS ALAMOS NM 87545

3 ENERGETIC MATERIALS RSCH CTR/DOE
NEW MEXICO INST OF MINING & TECH
ATTN DAVID J CHAVEZ
LARRY LIBERSKY
FRED SANDSTROM
CAMPUS STATION
SOCORRO NM 87801

1 NASA
LEWIS RESEARCH CENTER
ATTN J FERRANTE
CLEVELAND OH 44135

3 NASA
JOHNSON SPACE CENTER
ATTN ERIC CHRISTIANSEN
JEANNE LEE CREWS
FREDRICH HORZ
MAIL CODE SN3
2101 NASA RD 1
HOUSTON TX 77058

1 APPLIED RESEARCH LAB
ATTN JEFFREY A COOK
10000 BURNETT ROAD
AUSTIN TX 78758

1 GM RESEARCH LABS
ATTN J R SMITH
WARREN MI 48090

NO. OF
COPIES ORGANIZATION

5 JET PROPULSION LABORATORY
ATTN ZDENEK SEKANINA
PAUL WEISSMAN
BOB WEST
JAMES ZWISSLER
MARC ADAMS IMPACT PHYSICS GROUP
4800 OAK GROVE DR
PASADENA CA 91109

1 MAXWELL LABS
S CUBED DIVISION
ATTN GERALD A GURTMAN
PO BOX 1620
LA JOLLA CA 92037

1 AMES LABORATORY
IOWA STATE UNIVERSITY
ATTN J H ROSE
AMES IA 50011

1 CALIFORNIA ST UNIV
NORTHRIDGE
ATTN JON H SHIVELY
10343 4TH ST NW
ALBUQUERQUE NM 87114

2 CALTECH
ATTN ANDREW P INGERSOLL MS 170 25
THOMAS J AHRENS MS 252 21
1201 E CALIFORNIA BLVD
PASADENA CA 91125

1 CALTECH
ATTN GLENN ORTON MS 169 237
4800 OAK GROVE DR
PASADENA CA 91007

1 DREXEL UNIVERSITY
ATTN PHYSICS DEPT
32ND & CHESTNUT ST
PHILADELPHIA PA 19104

5 JOHNS HOPKINS UNIV
APPLIED PHYSICS LAB
ATTN TERRY R BETZER
ALVIN R EATON
RICHARD H KEITH
DALE K PACE
ROGER L WEST
JOHNS HOPKINS ROAD
LAUREL MD 20723

NO. OF
COPIES ORGANIZATION

1 LOUISIANA STATE UNIVERSITY
ATTN ROBERT W COURTER
948 WYLIE DR
BATON ROUGE LA 70808

1 MIT DEPT OF EARTH ATMOS AND
PLANETARY SCIENCES
ATTN HEIDI B HAMMELL 54 316
CAMBRIDGE MA 02139

1 NC STATE UNIVERSITY
ATTN YASUYUKI HORIE
RALEIGH NC 27695-7908

1 PENNSYLVANIA STATE UNIVERSITY
ATTN PHYSICS DEPT
UNIVERSITY PARK PA 16802

5 SOUTHWEST RESEARCH INSTITUTE
ATTN C ANDERSON
D LITTLEFIELD
S A MULLIN
B COUR PALAIS
J WALKER
PO DRAWER 28510
SAN ANTONIO TX 78284

1 STANFORD UNIVERSITY
ATTN BRIAN PETERSEN
RAINS 16L
704 CAMPUS DR
STANFORD CA 94305

1 TEXAS A&M UNIVERSITY
PHYSICS DEPARTMENT
ATTN DAN BRUTON
COLLEGE STATION TX 77843-4242

1 UC DAVIS
INST OF THEORETICAL DYNAMICS
ATTN E G PUCKETT
DAVIS CA 95616

1 UC SANTA BARBARA
INSTITUTE FOR THEORETICAL PHYSICS
ATTN F GUINEA
SANTA BARBARA CA 93106

NO. OF COPIES	ORGANIZATION
2	UNIV OF ALA HUNTSVILLE AEROPHYSICS RSCH CTR ATTN GARY HOUGH DAVID J LIQUORNIK PO BOX 999 HUNTSVILLE AL 35899
1	UNIV OF ALA HUNTSVILLE CIVIL ENGRNG DEPT ATTN WILLIAM P SCHONBERG HUNTSVILLE AL 35899
1	UNIV OF ALABAMA ATTN A EUGENE CARDEN 86 EASTERN HILLS COTTONDALE AL 35453
1	UNIVERSITY OF ARIZONA ATTN DAVID H LEVY TUCSON AZ 85721
1	UNIVERSITY OF CA BERKLEY MECHNL ENGRNING DEPT GRADUATE OFFICE ATTN KEZHUN LI BERKELEY CA 94720
1	UNIVERSITY OF CHICAGO DEPT OF THE GEOPHYSICAL SCIENCES ATTN G H MILLER 5734 S ELLIS AVE CHICAGO IL 60637
1	UNIVERSITY OF COLORADO ATTN T MACLAY CAMPUS BOX 431 NNT 341 BOULDER CO 80309
4	UNIVERSITY OF DELAWARE DEPT OF MECHANICAL ENGINEERING ATTN PROF J GILLESPIE DEAN R B PIPES PROF J VINSON PROF D WILKINS NEWARK DE 19716
1	UNIVERSITY OF MARYLAND ATTN PHYSICS DEPT (BLDG 082) COLLEGE PARK MD 20742

NO. OF COPIES	ORGANIZATION
1	UNIVERSITY OF PUERTO RICO DEPT CHEMICAL ENGINEERING ATTN L A ESTEVEZ MAYAGUEZ PR 00681-5000
1	UNIVERSITY OF TEXAS DEPT OF MECHANICAL ENGINEERING ATTN ERIC P FAHRENTHOLD AUSTIN TX 78712
1	ADVANCED TECHNOLOGY INC ATTN J ADAMS PO BOX 125 DAHLGREN VA 22448-0125
2	AEROJET ELECTRO SYS CO ATTN WARHEAD SYSTEMS J CARLEONE S KEY PO BOX 296 AZUSA CA 91702
2	AEROJET ORDNANCE ATTN P WOLF G PADGETT 1100 BULLOCH BLVD SOCORRO NM 87801
3	ALLIANT TECHSYSTEMS INC ATTN T HOLMQUIST MN11 2720 R STRYK G R JOHNSON MN11 2925 600 SECOND ST NE HOPKINS MN 55343
1	ALME AND ASSOCIATES ATTN MARVIN L ALME 6219 BRIGHT PLUME COLUMBIA MD 21044-3790
1	APPLIED RESEARCH ASSOC INC ATTN JEROME D YATTEAU 5941 S MIDDLEFIELD RD SUITE 100 LITTLETON CO 80123
1	APPLIED RESEARCH ASSOC INC ATTN FRANK MAESTAS 4300 SAN MATEO BLVD SE ALBUQUERQUE NM 87110

NO. OF COPIES	ORGANIZATION
1	BATTELLE ATTN ROBER M DUGAS 7501 S MEMORIAL PKWY SUITE 101 HUNTSVILLE AL 35802-2258
3	BATTELLE ATTN S GOLASKI R JAMESON TECHNICAL LIBRARY 505 KING AVE COLUMBUS OH 43201
3	BOEING AEROSPACE CO SHOCK PHYSICS & APPLIED MATH ENGINEERING TECHNOLOGY ATTN R HELZER T MURRAY J SHRADER PO BOX 3999 SEATTLE WA 98124
1	BOEING HOUSTON SPACE STN ATTN RUSSELL F GRAVES BOX 58747 HOUSTON TX 77258
1	BRIGS CO ATTN JOSEPH E BACKOFEN 2668 PETERSBOROUGH ST HERNDON VA 22071-2443
3	CALIFORNIA RSCH & TECHNOLOGY ATTN R BROWN R FRANZEN D ORPHAL 5117 JOHNSON DR PLEASANTON CA 94566
1	CALIFORNIA RSCH & TECHNOLOGY ATTN M MAJERUS PO BOX 2229 PRINCETON NJ 08543
1	COMPUTATIONAL MECHANICS CONSULTANTS ATTN J A ZUKAS PO BOX 11314 BALTIMORE MD 21239-0314

NO. OF COPIES	ORGANIZATION
1	DEFENSE TECHNOLOGY INTERNATIONAL INC ATTN D E AYER THE STARK HOUSE 22 CONCORD ST NASHUA NH 03060
1	DESKIN RESEARCH GROUP INC ATTN EDWARD COLLINS 2270 AGNEW RD SANTA CLARA CA 95054
2	EI DUPONT DE NEMOURS & CO ATTN L MINOR B SCOTT SECURITY DIR LEGAL DEPARTMENT PO BOX 1635 WILMINGTON DE 19899
1	G E DUVALL 5814 NE 82ND COURT VANCOUVER WA 98662-5944
3	DYNA EAST CORP ATTN P C CHOU R CICCARELLI W FLIS 3620 HORIZON DRIVE KING OF PRUSSIA PA 19406
3	DYNASEN ATTN JACQUES CHAREST MICHAEL CHAREST MARTIN LILLY 20 ARNOLD PL GOLETA CA 93117
1	ELORET INSTITUTE ATTN DAVID W BOGDANOFF MS 230 2 NASA AMES RESEARCH CENTER MOFFETT FIELD CA 94035
1	ENIG ASSOCIATES INC ATTN D J PASTINE 13230 INGLESIDE DR BELTSVILLE MD 20705
1	EXPLOSIVE TECHNOLOGY ATTN M L KNAEBEL PO BOX KK FAIRFIELD CA 94533

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
1	GB TECH LOCKHEED ATTN JAY LAUGHMAN 2200 SPACE PARK SUITE 400 HOUSTON TX 77258	3	KAMAN SCIENCES CORP ATTN SHELDON JONES GARY L PADEREWSKI ROBERT G PONZINI 1500 GRDN OF THE GODS RD COLORADO SPRINGS CO 80907
2	GB TECH LOCKHEED ATTN LUCILLE BORREGO C23C JOE FALCON JR C23C 2400 NASA ROAD 1 HOUSTON TX 77058	4	KAMAN SCIENCES CORP ATTN NASIT ARI STEVE R DIEHL WILLIAM DOANE VERNON M SMITH PO BOX 7463 COLORADO SPRINGS CO 80933-7463
2	GENERAL RESEARCH CORP ATTN A CHARTERS T MENNA PO BOX 6770 SANTA BARBARA CA 93160-6770	1	D R KENNEDY & ASSOC INC ATTN D KENNEDY PO BOX 4003 MOUNTAIN VIEW CA 94040
2	GRC INTERNATIONAL ATTN TIMOTHY M CUNNINGHAM WILLIAM M ISBELL 5383 HOLLISTER AVE SANTA BARBARA CA 93111	1	KERLEY PUBLISHING SERVICES ATTN G I KERLEY PO BOX 13835 ALBUQUERQUE NM 87192-3835
5	INST OF ADVANCED TECHNOLOGY UNIVERSITY OF TX AUSTIN ATTN STEPHEN J BLESS JAMES CAZAMIAS HARRY D FAIR THOMAS M KIEHNE NICK LYNCH 4030-2 W BRAKER LN AUSTIN TX 78759	2	KTECH CORPORATION ATTN FRANK W DAVIES LARRY M LEE 901 PENNSYLVANIA NE ALBUQUERQUE NM 87110
1	KAMAN SCIENCES CORP ATTN DENNIS L JONES 2560 HUNTINGTON AVE SUITE 200 ALEXANDRIA VA 22303	1	LIVERMORE SOFTWARE TECH CORP ATTN J O HALLQUIST 2876 WAVERLY WAY LIVERMORE CA 94550
8	KAMAN SCIENCES CORP ATTN J ELDER RICHARD P HENDERSON DAVID A PYLES FRANK R SAVAGE JAMES A SUMMERS JAMES S WILBECK TIMOTHY W MOORE THY YEM 600 BLVD S SUITE 208 HUNTSVILLE AL 35802	1	LOCKHEED ENGRNG & SPC SCIENCES ATTN E CYKOWSKI MS B22 2400 NASA RD 1 HOUSTON TX 77058
		1	LOCKHEED MARTIN MISSILE & SPACE ATTN WILLIAM R EBERLE PO BOX 070017 HUNTSVILLE AL 35807

NO. OF
COPIES ORGANIZATION

3 LOCKHEED MARTIN MISSILE & SPACE
ATTN M A LEVIN ORG 81 06 BLDG 598
M R MCHENRY
T A NGO ORG 81 10 BLDG 157
111 LOCKHEED WAY
SUNNYVALE CA 94088

4 LOCKHEED MISSILE & SPACE CO
ATTN JOHN R ANDERSON
WILLIAM C KNUDSON
S KUSUMI 0 81 11 BLDG 157
J PHILLIPS 0 54 50
PO BOX 3504
SUNNYVALE CA 94088

1 LOCKHEED MISSILE & SPACE CO
ATTN R HOFFMAN
SANTA CRUZ FACILITY
EMPIRE GRADE RD
SANTA CRUZ CA 95060

1 LOCKHEED NASA JSC
SPACE SCIENCE BRANCH
ATTN JAMES HYDE
BOX 58561 MC B22
HOUSTON TX 77258

1 LOCKHEED MARTIN AEROSPACE
ATTN D R BRAGG
PO BOX 5837 MP 109
ORLANDO FL 32855

1 MCDONNELL DOUGLAS
ASTRONAUTICS CO
ATTN B L COOPER
5301 BOLSA AVE
HUNTINGTON BEACH CA 92647

1 ORLANDO TECHNOLOGY INC
ATTN DANIEL A MATUSKA
PO BOX 855
SHALIMAR FL 32579

1 PHYSICAL SCIENCES INC
ATTN PETER NEBOLSINE
20 NEW ENGLAND BUS CTR
ANDOWER MA 01810

NO. OF
COPIES ORGANIZATION

3 PHYSICS INTERNATIONAL
ATTN R FUNSTON
G FRAZIER
L GARNETT
PO BOX 5010
SAN LEANDRO CA 94577

1 ROCKWELL INTERNATIONAL
ROCKETDYNE DIVISION
ATTN J MOLDENHAUER
6633 CANOGA AVE HB 23
CANOGA PARK CA 91303

1 ROCKWELL INTERNATIONAL
ROCKETDYNE DIVISION
ATTN H LEIFER
16557 PARK LN CIRCLE
LOS ANGELES CA 90049

1 ROCKWELL MISSILE SYS DIV
ATTN T NEUHART
1800 SATELLITE BLVD
DULUTH GA 30136

1 S CUBED
ATTN R SEDGWICK
PO BOX 1620
LA JOLLA CA 92038-1620

1 SAIC
ATTN GREGORY J STRAUCH MS 264
1710 GOODRIDGE DR
MCLEAN VA 22102

1 SAIC
ATTN MICHAEL W MCKAY
10260 CAMPUS POINT DR
SAN DIEGO CA 92121

1 SHOCK TRANSIENTS INC
ATTN DAVID DAVISON
BOX 5357
HOPKINS MN 55343

2 SIMULATION & ENG CO INC
ATTN ELSA I MULLINS
STEVEN E MULLINS
8840 HWY 20 SUITE 200 N
MADISON AL 35758

NO. OF COPIES	ORGANIZATION
2	SOUTHERN RESEARCH INSTITUTE ATTN LINDSEY A DECKARD DONALD P SEGERS PO BOX 55305 BIRMINGHAM AL 35255-5305
4	SRI INTERNATIONAL ATTN JAMES D COLTON MOHSEN SANAI DR L SEAMAN DONALD A SHOCKLEY 333 RAVENSWOOD AVE MENLO PARK CA 94025
3	TELEDYNE BROWN ENGR ATTN JIM W BOOTH MARTIN B RICHARDSON SHERRY RIDDLE PO BOX 070007 MS 50 HUNTSVILLE AL 35807-7007
1	ZERNOW TECHNICAL SVCS INC ATTN LOUIS ZERNOW 425 W BONITA AVE SUITE 208 SAN DIMAS CA 91773

NO. OF COPIES	ORGANIZATION
	<u>ABERDEEN PROVING GROUND</u>
37	DIR, USARL ATTN: AMSRL-WM, I. MAY AMSRL-WM-T, W. F. MORRISON AMSRL-WM-TA, W. BRUCHEY J. DEHN G. FILBEY W. GILLICH W. A. GOOCH H. W. MEYER E. J. RAPACKI AMSRL-WM-TB, R. FREY J. STARKENBERG AMSRL-WM-TC, W. S. DE ROSSET T. W. BJERKE R. COATES F. GRACE K. KIMSEY M. LAMPSON D. SCHEFFLER S. SCHRAML B. SORENSEN R. SUMMERS W. WALTERS AMSRL-WM-TD, A. M. DIETRICH K. FRANK J. HARRISON M. RAFTENBERG G. RANDERS-PEHRSON J. SANTIAGO M. SCHEIDLER S. SEGLETES (3 CP) J. WALTER T. WRIGHT AMSRL-WM-PB, A. ZIELINSKI AMSRL-WM-PD, G. GAZONAS AMSRL-WM-WD, A. PRAKASH

NO. OF
COPIES ORGANIZATION

- 1 ABTEILUNG FUER PHYSIKALISCHE
CHEMIE
MONT ANUNIVERSITAET
ATTN E KOENIGSBERGER
A 8700 LOEBEN
AUSTRIA
- 2 AWE
ATTN MICHAEL GERMAN
WAYNE HARRISON
FOULNESS ESSEX SS3 9XE
UNITED KINGDOM
- 1 BATTELLE INGENIEUTECHNIK GMBH
DUESSELDORFFER STR 9
ESCHBORN D 65760
GERMANY
- 1 BHABHA ATOMIC RESEARCH CENTRE
HIGH PRESSURE PHYSICS DIVISION
ATTN N SURESH
TROMBAY BOMBAY 400 085
INDIA
- 1 BULGARIAN ACADEMY OF SCIENCES
SPACE RESEARCH INSTITUTE
ATTN VALENTIN GOSPODINOV
1000 SOFIA PO BOX 799
BULGARIA
- 1 CANADIAN ARSENALS LTD
ATTN P PELLETIER
5 MONTEE DES ARSENAUX
VILLIE DE GRADEUR PQ J5Z2
CANADA
- 1 CEA
ATTN ROGER CHERET
CEDEX 15
313 33 RUE DE LA FEDERATION
PARIS 75752
FRANCE
- 1 CEA
CISI BRANCH
ATTN PATRICK DAVID
CENTRE DE SACLAY BP 28
GIF SUR YVETTE 91192
FRANCE

NO. OF
COPIES ORGANIZATION

- 1 CEA/CESTA
ATTN ALAIN GEILLE
BOX 2 LE BARP 33114
FRANCE
- 3 CENTRE D'ETUDES DE GRAMAT
ATTN SOLVE GERARD
CHRISTIAN LOUPIAS
PASCALE OUTREBON
GRAMAT 46500
FRANCE
- 2 CENTRE D'ETUDES DE LIMEIL-VALENTON
ATTN CHRISTIAN AUSSOURD
JEAN-CLAUDE BOZIER
SAINT GEORGES CEDEX
VILLENEUVE 94195
FRANCE
- 3 CENTRE D'ETUDES DE VAUJOURS
ATTN PLOTARD JEAN-PAUL
ERIC BOTTET
TAT SIHN VONG
BOITE POSTALE NO 7
COUNTRY 77181
FRANCE
- 1 CENTURY DYNAMICS LTD
ATTN NIGEL FRANCIS
12 CITY BUSINESS CTR
BRIGHTON RD HORSHAM
WEST SUSSEX RH1354BA
UNITED KINGDOM
- 1 CRC RESEARCH INST INC
ATTN MASAHIKE KATAYAMA
STRUCTURAL ENGINEERING DEPT
1 3 316 NAKASE MIHAMA KU
CHIBA SHI 261 01
JAPAN
- 1 DAT ETBS CETAM
ATTN CLAUDE ALTMAYER
ROUTE DE GUERRY BOURGES
18015
FRANCE

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	DEFENCE RESEARCH AGENCY ATTN W A J CARSON CHOBHAM LANE CHERTSEY SURREY KT16 0EE UNITED KINGDOM
1	DEFENCE RESEARCH AGENCY ATTN DAVID HAFFENDEN FORT HALSTEAD SEVENOAKS KENT TN14 7BP UNITED KINGDOM
1	DEFENCE RSCH ESTAB SUFFIELD ATTN D MACKAY RALSTON ALBERTA TOJ 2NO RALSTON CANADA
1	DEFENCE RSCH ESTAB SUFFIELD ATTN CHRIS WEICKERT BOX 4000 MEDICINE HAT ALBERTA T1A 8K6 CANADA
1	DEFENCE RSCH ESTAB VALCARTIER ATTN N GASS PO BOX 8800 COURCELETTE PQ GOA IRO CANADA
4	DEPARTAMENTO DE QUIMICA FISICA FACULTAD DE CIENCIAS QUIMICAS UNIVERSIDAD COMPLUTENSE DE MADRID ATTN V G BAONZA M TARAVILLO M CACERAS J NUNEZ 28040 MADRID SPAIN
1	DYNAMIC RESEARCH AB ATTN AKE PERSSON PARADISGRAND 7 SODERTALJE S 151 36 SWEDEN

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
4	ERNST MACH INSTITUT ATTN VOLKER HOHLER E SCHMOLINSKE E SCHNEIDER A J STILP ECKERSTRASSE 4 D-7800 FREIBURG I BR 791 4 GERMANY
1	ESTEC CS ATTN DOUGLAS CASWELL BOX 200 NOORDWIJK 2200 AG NETHERLANDS
1	EUROPEAN SPACE AGENCY ATTN WALTER FLURY ESOC 5 ROBT BOSCHT STRASSE DARMSTADT 6100 GERMANY
2	EUROPEAN SPACE AGENCY ESTEC ATTN LUCY BERTHOUD MICHEL LAMBERT POSTBUS BOX 299 NOORDWIJK NL2200 AG NETHERLANDS
1	FRENCH GERMAN RESEARCH INST ATTN HARTMUTH F LEHR POSTFACH 1260 WEIL AM RHEIN D-79574 GERMANY
3	FRENCH GERMAN RESEARCH INST ATTN HANS-JURGEN ERNST FRANCIS JAMET PASCALE LEHMANN CEDEX 5 5 RUE DU GENERAL CASSAGNOU SAINT LOUIS 68301 FRANCE

NO. OF
COPIES ORGANIZATION

- 4 HIGH ENERGY DENSITY RESEARCH CTR
ATTN VLADIMIR E FORTOV
GENADII I KANEL
V A SKVORTSOV
O YU VOJOBIEV
IZHORSKAJA STR 13/19
MOSCOW 127412
RUSSIAN REPUBLIC
- 3 IABG
ATTN H J RAATSCHEN
W SCHITTKE
F F SCHARPPF
EINSTEINSTRASSE 20
D 8012 OTTOBRUN B MUENCHEN
GERMANY
- 3 IABG
ATTN M BORRMANN
HEINRICH G DORSCH
H J RAATSCHEN
EINSTENSTRASSE 20
OTTOBRUN D 85521
GERMANY
- 1 IFAM
ATTN LOTHAR MEYER
LESUMER HEERSTRASSE 36
BREMEN 77
GERMANY
- 1 INSTITUTE FOR PROBLEMS OF STRENGTH
ATTN G STEPANOV
TIMIRYAZEVS KAYU STR 2
252014 KIEV
UKRAINE
- 1 INSTITUTE OF CHEMICAL PHYSICS
ATTN A YU DOLGOBORODOV
KOSYGIN ST 4 V 334
MOSCOW
- 2 INSTITUTE OF CHEMICAL PHYSICS
RUSSIAN ACADEMY OF SCIENCES
ATTN A M MOLODETS
S RAZORENOV
142432 CHERNOGOLOVKA
MOSCOW REGION
RUSSIAN REPUBLIC

NO. OF
COPIES ORGANIZATION

- 2 IOFFE PHYSICO TECHNICAL INSTITUTE
DENSE PLASMA DYNAMICS
LABORATORY
ATTN EDWARD M DROBYSHEVSKI
A KOZHUSHKO
ST PETERSBURG 194021
RUSSIAN REPUBLIC
- 1 IPE RAS
ATTN A A BOGOMAZ
DVORTSOVAIA NAB 18
ST PETERSBURG
RUSSIAN REPUBLIC
- 1 ISL
ATTN CHANTERET PIERRE-YVES
F68301 SAINT-LOUIS
CEDEX 12 RUE DE L'INDUSTRIE
BP 301
FRANCE
- 1 LABORATOIRE DE TECHNOLOGIE DES
SURFACES
ECOLE CENTRALE DE LYON
ATTN PASCAL VINET
BP 163
69131 ECULLY CEDEX
FRANCE
- 2 LAVRENTYEV INST. HYDRODYNAMICS
ATTN LEV A MERZHIEVSKY
VICTOR V SILVESTROV
NOVOSIBIRSK 630090
RUSSIAN REPUBLIC
- 1 MOSCOW INST OF PHYSICS & TECH
ATTN S V UTUZHNIKOV
DEPT OF COMPUTATIONAL MATHEMATICS
DOLGOPRUDNY 1471700
RUSSIAN REPUBLIC
- 1 NATL DEFENCE DENSITY RSCH CTR
ATTN JOHAN FORSS
FOA FOX 551
TUMBA S 14725
SWEDEN

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
3	NATL DEFENCE RESEARCH EST ATTN LARS HOLMBERG ULF LINDEBERG LARS GUNNAR OLSSON FOA BOX 551 TUMBA S 14725 SWEDEN	1	TECHNISCHE UNIVERSITAT MUENCHEN ATTN EDUARD B IGENBERGS RICHARD WAGNER STR 18 111 MUENCHEN 2 D8000 GERMANY
1	PML TNO ATTN EDWARD VAN RIET BOX 45 RIJSWIJK 2230AA NETHERLANDS	1	TOMSK BRANCH OF THE INSTITUTE FOR STRUCTURAL MACROKINETICS ATTN V GORELSKI 8 LENIN SQ GSP 18 TOMSK 634050 RUSSIAN REPUBLIC
1	PRB S A ATTN M VANSNICK AVENUE DE Tervueren 168 BTE 7 BRUSSELS B 1150 BELGIUM	1	UK MINISTRY OF DEFENCE ATTN GRAHAM J CAMBRAY CBDE PORTON DOWN SALISBURY WITTSHERE SPR 0JQ UNITED KINGDOM
1	PRINS MAURITS LABORATORY ATTN H J REITSMA TNO BOX 45 RIJSWIJK 2280AA NETHERLANDS	1	UNIVERSIDAD DE CANTABRIA FACULTAD DE CIENCIAS DEPARTAMENTO DE FISICA APLICADA ATTN J AMOROS AVDA DE LOS CASTROS S/N SANTANDER SPAIN
2	RAFAEL BALLISTICS CENTER ATTN EREZ DEKEL YEHUDA PARTOM PO BOX 2250 HAIFA 31021 ISRAEL	1	UNIVERSIDAD DE OVIEDO FACULTAD DE QUIMICA DEPARTAMENTO DE QUIMICA FISICA Y ANALITICA ATTN E FRANCISCO AVENIDA JULIAN CLAVERIA S/N 33006 - OVIEDO SPAIN
1	RESEARCH INSTITUTE OF MECHANICS NIZHNIY NOVGOROD STATE UNIVERSITY ATTN A SADYRIN P R GAYARINA 23 KORP 6 NIZHNIY NOVGOROD 603600 RUSSIAN REPUBLIC	1	UNIVERSITY OF GUELPH PHYSICS DEPT ATTN C G GRAY GUELPH ONTARIO N1G 2W1 CANADA
1	ROYAL ARMAMENT R&D ESTAB ATTN I CULLIS FORT HALSTEAD SEVENOAKS KENT TN14 7BJ UNITED KINGDOM	2	UNIVERSITY OF KENT UNIT FOR SPACE SCIENCES ATTN PHILIPPE GENTA PAUL RATCLIFF CANTERBURY KENT CT2 7NR UNITED KINGDOM
1	SAMARA STATE AEROSPACE UNIV ATTN L G LUKASHEV SAMARA RUSSIAN REPUBLIC		

INTENTIONALLY LEFT BLANK

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE November 1996		3. REPORT TYPE AND DATES COVERED Final, 18 July - 5 August 1996
4. TITLE AND SUBTITLE An Equation of State for Metals			5. FUNDING NUMBERS PR: 1L162618AH80	
6. AUTHOR(S) Steven B. Segletes				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WM-TD Aberdeen Proving Ground, MD 21005-5066			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-1270	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)			10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A new analytical equation of state is offered for metals. The form is expressible completely in terms of the maximum lattice vibration frequency, macroscopically expressible as the characteristic temperature, Θ , and its derivatives. For one particularly useful special case, the results have been found to match both cold-curve and shock-Hugoniot data for a variety of metals. The equation is of the Grüneisen variety, in which the Grüneisen parameter is specified as a function of volume only. The equation begins to lose accuracy in the pressure range of one to several megabars, perhaps because of the breakdown of the Grüneisen assumption, whereupon the Grüneisen parameter becomes energy dependent.				
14. SUBJECT TERMS equation of state, lattice frequency, Grüneisen, Debye temperature			15. NUMBER OF PAGES 58	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

INTENTIONALLY LEFT BLANK

USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number/Author ARL-TR-1270 (Segletes) Date of Report November 1996

2. Date Report Received _____

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) _____

4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) _____

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. _____

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) _____

CURRENT
ADDRESS

Organization

Name

E-mail Name

Street or P.O. Box No.

City, State, Zip Code

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

OLD
ADDRESS

Organization

Name

Street or P.O. Box No.

City, State, Zip Code

(Remove this sheet, fold as indicated, tape closed, and mail.)

(DO NOT STAPLE)

DEPARTMENT OF THE ARMY


OFFICIAL BUSINESS

BUSINESS REPLY MAIL

FIRST CLASS PERMIT NO 0001,APG,MD

POSTAGE WILL BE PAID BY ADDRESSEE

**DIRECTOR
US ARMY RESEARCH LABORATORY
ATTN AMSRL WM TD
ABERDEEN PROVING GROUND MD 21005-5066**



**NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES**

